



# PUSHING BOUNDARIES TO CO-CREATE A HIGHER QUALITY OF LIFE

GGB helps create a world of motion with minimal frictional loss through plain bearing and surface engineering technologies. With R&D, testing and production facilities in the United States, Germany, France, Brazil, Slovakia and China, GGB partners with customers worldwide on customized tribological design solutions that are efficient and environmentally sustainable. GGB's engineers bring their expertise and passion for tribology to a wide range of industries, including automotive, aerospace and industrial manufacturing. To learn more about tribology for surface engineering from GGB, visit <a href="https://www.ggbearings.com">www.ggbearings.com</a>.

Our products are used in tens of thousands of critical applications every day on our planet. It is always our goal to provide superior, high-quality solutions for our customers' needs, no matter where those demands take our products. From space vehicles to golf carts and virtually everything in between; we offer the industry's most extensive range of high performance, maintenance-free bearing solutions for a multitude of applications:

- Aerospace - Construction - Fluid Power - Mining - Railway

Agricultural
 E-Mobility
 Industrial
 Oil & Gas
 Recreation

- Automotive - Energy - Medical - Primary Metals

# The GGB Advantage





#### **LOWER SYSTEM COST**

GGB bearings reduce shaft costs by eliminating the need for hardening and machining grease paths. Their compact, one-piece construction provides space and weight savings and simplifies assembly.



#### LOW-FRICTION, HIGH WEAR RESISTANCE

Low coefficients of friction eliminate the need for lubrication, while providing smooth operation, reducing wear and extending service life. Low-friction also eliminates the effects of stick-slip or "stiction" during start up.



#### **MAINTENANCE-FREE**

GGB bearings are self-lubricating, making them ideal for applications requiring long bearing life without continuous maintenance, as well as operating conditions with inadequate or no lubrication.



#### **ENVIRONMENTAL**

Greaseless, lead-free GGB bearings comply with increasingly stringent environmental regulations such as the EU RoHS directive restricting the use of hazardous substances in certain types of electrical and electronic equipment.



#### **CUSTOMER SUPPORT**

GGB's flexible production platform and extensive supply network assure quick turnaround and timely deliveries. In addition, we offer local applications engineering and technical support.





# The Highest Standards in Quality

Our world-class manufacturing plants in the United States, Brazil, China, Germany, France and Slovakia are certified in quality and excellence according to ISO 9001, IATF 16949, ISO 14001 and ISO 45001. This allows us to access the industry's best practices while aligning our management system with global standards.

For a complete listing of our certifications, please visit our website: www.ggbearings.com/en/company/certificates

# Tribology at GGB

# BY MAKING ADVANCEMENTS IN THE FIELD OF TRIBOLOGY, WE CAN:

- Reduce/control friction, decrease wear, increase lifetime and durability - Lower overall operating cost
- Reduce energy losses Make our world a little greener
- Reduce/control stick-slip, improve precision and reduce noise Keep people safe, improve comfort and quality of life















### Who we Are



#### TIMKEN AND GGB: EXPONENTIAL EXPERTISE AND INNOVATION

Timken has completed 24 acquisitions since 2010 to advance its engineered bearings and industrial motion expertise. The latest, GGB, provides additional technical solutions that strengthen Timken's position in key strategic markets.

At GGB, engineers apply specialized knowledge in material science and tribology to innovate polymer coatings and plain bearing solutions for industrial applications, including pumps and compressors, HVAC, off-highway, energy, material handling and aerospace. With its acquisition of GGB, Timken diversifies its technical expertise and global leadership in highly engineered bearings — giving customers access to more custom bearing solutions across more markets.

#### **Exponential innovation for shifting design trends**

Andreas Roellgen, executive vice president and president of the Engineered Bearings group, said the GGB acquisition builds on Timken's "advanced coating technologies and customized solutions for customers' specific needs in fragmented markets". While every acquisition is about adding value for customers, the more synergies there are, the greater the potential.

"Timken has very strong capabilities in material science, surface engineering and tribology — specific to steel-made bearings with rolling elements," said Roellgen. "GGB builds on strengthening knowledge beyond steel-bearing competencies in all three areas that help address emerging technical trends for our customers."

Two such trends are light-weighting and downsizing in applications like electric vehicles and wind energy. GGB plain bearing solutions help with this by using a wide range of materials like polymer coatings, engineered plastics, fiber-reinforced composites and bimetals.

In many cases, the two companies engineer adjacent, ultra-high-performance solutions for the same customers and equipment.

For example, the Curiosity rover has been operating on Mars for 10+ years and depends on GGB self-lubricating metal-polymer bushings to help drill for rock samples. Also onboard are two ¼ inch (6.35 mm) Timken bearings that run a vacuum pump in support of the rover's analytical equipment. Essentially, GGB helps gather the samples, and Timken makes it possible to learn about them. Both are crucial to mission success.

#### Shared legacy, complementary products

GGB was founded in 1899, the same year Timken began producing its first patented tapered roller bearing. Also similar to Timken, GGB demonstrated early leadership in key markets, inventing the first self-lubricated metal-polymer bearing, and they are recognized for their excellence in application engineering.

Chris Small, president, GGB, added that this is what sets GGB apart in the global plain bearings market.

"It's extremely competitive, but we're able to win customers because our strong application engineering capabilities and our legacy of material science innovations," he said. "Collaborating with customers, designing into their applications and solving their most critical problems brings so much loyalty."

And like Timken, GGB has a global manufacturing footprint committed to safety, quality and efficiency, in support of an ever-evolving product line.

"GGB will have a noteworthy impact due to its size and scope, Roellgen said. They have capabilities and products new to our customers. We have the channel access to get them into new market spaces. From a customer value creation standpoint, it's quite exciting."

# Overview of Bearing Materials & Accessory Products

### **TRIBOLOGICAL COATINGS**

PRODUCT NAME	POLYMER COATINGS	WORKING CONDITIONS	PAGE
TriboShield®TS161	TriboShield coatings are applied directly to the customer's part	low-friction, low-loads	9
TriboShield®TS225	TriboShield coatings are applied directly to the customer's part	low-friction, low to medium loads	10
TriboShield®TS421	TriboShield coatings are applied directly to the customer's part	low-friction, low-loads	11
TriboShield®TS651	TriboShield coatings are applied directly to the customer's part	low-friction, up to moderately high loads	3 12
TriboShield®TS741	TriboShield coatings are applied directly to the customer's part	low-friction, moderate up to high loads	13

### **TRIBOLOGICAL BEARINGS**

PRODUCT NAME	METAL-POLYMER BEARINGS	WORKING CONDITIONS	PAGE
DP4®	Steel + Porous Bronze Sinter + PTFE + Fillers	self-lubricating, low-maintenance	14
DP4-B	Bronze + Porous Bronze Sinter + PTFE + Fillers	self-lubricating, corrosion-resistant	15
<u>DU</u> ®	Steel + Porous Bronze Sinter + PTFE + Pb	self-lubricating	16
DU-B	Bronze + Porous Bronze Sinter + PTFE + Pb	self-lubricating, corrosion-resistant	17
DP10	Steel + Porous Bronze Sinter + PTFE + Solid Lubricants	self-lubricating, low-maintenance	18
<u>DP11</u>	Steel + Porous Bronze Sinter + PTFE + Solid Lubricants + Fillers	self-lubricating, low-maintenance	19
DP31	Steel + Porous Bronze Sinter + PTFE + Fluoropolymer + Fillers	low-maintenance	20
DX®	Steel + Porous Bronze Sinter + POM with Lubrication indents	low-maintenance, machinable	21
DX®10	Steel + Porous Bronze Sinter + High Tech Polymer with Lubrication indents	low-maintenance, machinable	22
HI-EX®	Steel + Porous Bronze Sinter + PEEK + PTFE + Fillers	low-maintenance, machinable	23
DTS10 <sup>®</sup>	Steel + Porous Bronze Sinter + PTFE + Fillers	low-maintenance, machinable	24
<u>DS</u>	Steel + Porous Bronze Sinter + POM Modified	self-lubricating, low-maintenance	25

h

PRODUCT NAME	ENGINEERED PLASTIC BEARINGS	WORKING CONDITIONS	PAGE
EP®	PA6.6T + Solid Lubricant + Fillers	self-lubricating	26
EP®12	POM + Solid Lubricant	self-lubricating	27
EP®15	POM + Solid Lubricant	self-lubricating	28
EP®22	PBT + Solid Lubricant	self-lubricating	29
EP®30	PA 6.6 + AF + Solid Lubricant	self-lubricating	30
EP®43	PPS + Solid Lubricant + Fillers	self-lubricating	31
EP®44	PPS + Solid Lubricant + Fillers	self-lubricating	32
EP®63	PEEK + Solid Lubricant + Fillers	self-lubricating	33
EP®64	PEEK + Solid Lubricant + Fillers	self-lubricating	34
EP®73	PAI + Solid Lubricant + Fillers	self-lubricating	35
EP®79	PAI + Solid Lubricant + Fillers	self-lubricating	36
KA Glacetal	POM	self-lubricating, low-maintenance	37
Multilube	POM + Solid Lubricant + Fillers	self-lubricating	38

PRODUCT NAME	FIBER REINFORCED COMPOSITE BEARINGS	WORKING CONDITIONS	PAGE
GAR-MAX®	Continuous wound PTFE and high-strength fibers encapsulated in an internally lubricated, high temperature filled epoxy resin sliding layer + continuous wound fiberglass encapsulated in a high temperature epoxy resin	self-lubricating	39
GAR-FIL	Proprietary filled PTFE tape liner + continuous wound fiberglass encapsulated in a high temperature epoxy resin	self-lubricating	40
HSG	Continuous wound PTFE and high-strength fibers encapsulated in an internally lubricated, high temperature filled epoxy resin sliding layer + continuous wound fiberglass encapsulated in a high temperature epoxy resin	self-lubricating	41
MLG	Continuous wound PTFE and high-strength fibers encapsulated in an internally lubricated, high temperature filled epoxy resin sliding layer + continuous wound fiberglass encapsulated in a high temperature epoxy resin	self-lubricating	42
НРМ	Continuous wound PTFE and high-strength fibers encapsulated in an internally lubricated, high temperature filled epoxy resin sliding layer + continuous wound fiberglass encapsulated in a high temperature epoxy resin	self-lubricating	43
HPMB <sup>®</sup>	Machinable continuous wound PTFE and high-strength fibers encapsulated in an internally lubricated, high temperature filled epoxy resin sliding layer + continuous wound fiberglass encapsulated in a high temperature epoxy resin	self-lubricating	44
HPE	Proprietary filled PTFE tape liner + continuous woven cloth laminate impregnated and cured with epoxy resin	self-lubricating	45
GGB- MEGALIFE®XT	Proprietary filled PTFE tape liner on both sides + continuously woven layer of filament glass fiber encapsulated in a high temperature epoxy resin	self-lubricating	46
Multifil	PTFE + proprietary filler system	self-lubricating	47
SBC with GAR-MAX®	Composite material with sealing SBC bearings are available with GAR-MAX are sealed to exclude containments. SBC are optionally available with a steel outer shell.	self-lubricating, low-maintenance	48
SBC with HSG	Composite material with sealing SBC bearings are available with HSG are sealed to exclude containments. SBC are optionally available with a steel outer shell.	self-lubricating, low-maintenance	49

# Overview of Bearing Materials & Accessory Products

PRODUCT NAME	METAL & BIMETAL BEARINGS	WORKING CONDITIONS	PAGE
GGB-CSM <sup>®</sup>	Powder metallurgical monometallic bearing material (bronze, nickel or iron-based) + solid graphite lubricant, MoS <sub>2</sub>	self-lubricating	50
GGB-CBM®	Thin walled powder metallurgical bimetal bearing material stainless steel, carbon steel or bronze with bronze + based backing): + solid graphite lubricant	self-lubricating	51
GGB-BP25	Sintered bronze impregnated with oil, similar to SINT A 50, impregnation group 1	self-lubricating	52
GGB-FP20	Steel alloy sinter impregnated with oil, similar to SINT A 10, impregnation group 1	self-lubricating	53
GGB-S016	Sintered steel alloy impregnated with oil	self-lubricating	54
GGB-SHB®	Case hardened steel bearings for lubricated applications	conventional lubrication	55
AuGlide	Steel backing and lead-free bronze overlay	low-maintenance	56
SY	Steel backing and leaded bronze overlay + CuPb10Sn10	low-maintenace	57
SP	Steel backing and leaded bronze overlay + CuPb26Sn2	low-maintenance	58
MBZ-B09	Monometallic material CuSn8	self-lubricating	59
LD®	Monometallic material CuSn8	self-lubricating	60
LDD®	Monometallic material CuSn8	self-lubricating	61
GGB-DB®	Dry bearing material: cast bronze + solid lubricant inserts	self-lubricating	62

### **ACCESSORY PRODUCTS**

PRODUCT NAME	BEARING ASSEMBLIES	PAGE
UNI	Self-aligning bearing housings	63
MINI	Self-aligning bearing housings	64
EXALIGN®	Self-aligning bearing housings	65

ADDITIONAL INFORMATION	PAGE
Technical Data Sheet	66
Product Information / Fabrication	67

Ö

# TriboShield®TS161 Polymer Coating



### SELF-LUBRICATING COMPOSITE COATING FOR LOW LOADS

TS161 is an engineering thermoplastic based composite coating composed of a primer and a top coat. Specifically designed for low-friction at low loading conditions, it presents excellent wear resistance as one of its standout features. TS161 is part of the standard TriboShield® product range.

#### **UNIQUE CHARACTERISTICS**

- Low-friction in low loading conditions
- Excellent wear resistance under low loads

BEARING PROPERTIES	UNITS	VALUE
GENERAL		
Color		Black
Max. continuous service temperature	°C/°F	60 / 140
Max. short-term peak temperature	°C/°F	80 / 176
Friction coefficient, typical range*		0.04 - 0.25
Food contact compliant**		No

Dependent on contact pressure, sliding speed and contact geometry.

#### **AVAILABILITY**

TriboShield coatings are applied directly to the customer's part. Suitable for complex geometries and a wide range of substrates eg steel, stainless steel, Al, Ti, Mg etc. Can be used for both interacting surfaces that are in relative motion


#### TYPICAL APPLICATIONS

- Conveyor deflectors
- Rod guides
- Automotive seat belt sliders
- Sliding guides for packaging lines

#### TRIBOMATE® UPGRADE AVAILABLE

No

### TriboShield® Standard Product Range

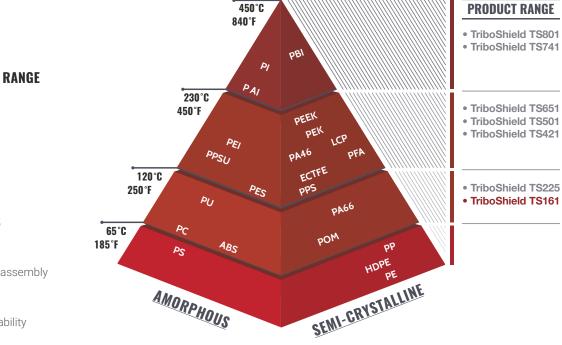

#### STANDARD COATINGS RANGE

PERFORMANCE
PROCESSING
COMPLEXITY
COST

- More compact design
- Less complex system assembly
- Reduced weight
- Increased surface durability

<sup>\*\*</sup> Your specific food contact condition may require additional approval. Please contact your GGB representative for more information.

# TriboShield®TS225 Polymer Coating



#### NANOSTRUCTURED COATING FOR LOW TO MEDIUM LOADS

TS225 is based on a nanostructured thermoset polymer designed for low-friction and high wear resistance at low to medium loads in dry or lubricated conditions. TS225 is part of the standard TriboShield® product range.

#### **UNIQUE CHARACTERISTICS**

- Excellent friction at high sliding speeds
- Very good friction in lubricated conditions
- Applicable to heat-sensitive substrates
- High surface hardness

#### **AVAILABILITY**

TriboShield coatings are applied directly to the customer's part and are suitable for complex geometries as well as various substrates e.g. steel, stainless steel, Al, Ti, Mg, etc. They can be used for both interacting surfaces that are in relative motion

#### TYPICAL APPLICATIONS


- Piston skirts for internal combustion engines
- Garden and DYI tools

#### TRIBOMATE® UPGRADE AVAILABLE

Yes

UNITS	VALUE
	Black
°C/°F	120 / 248
°C/°F	130 / 266
	0.04 - 0.25
	No
	°C/°F

### TriboShield® Standard Product Range

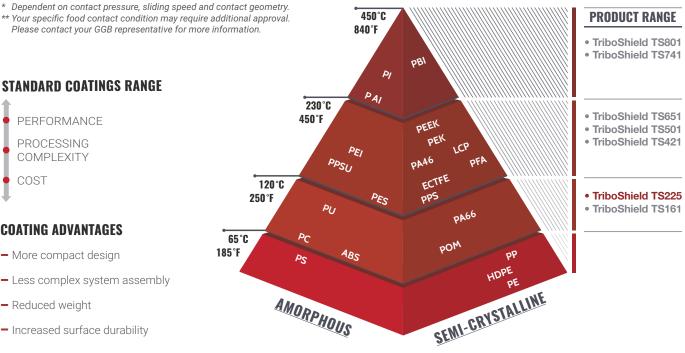

#### STANDARD COATINGS RANGE

PERFORMANCE **PROCESSING** COMPLEXITY COST

- More compact design
- Less complex system assembly
- Reduced weight
- Increased surface durability

# TriboShield®TS421 Polymer Coating



#### **LOW-FRICTION COATING** FOR LUBRICATED CONDITIONS

TS421 is based on engineering thermoplastics, specifically designed for extremely low-friction in lubricated conditions under low loads but presenting good characteristics in dry low load conditions as well. This system comprises a primer layer and an active hybrid top-coat. TS421 is part of the standard TriboShield® product range.

#### **UNIQUE CHARACTERISTICS**

- Extremely low-friction in lubricated condition
- Very low-friction in dry conditions at low loads
- Excellent chemical resistance

BEARING PROPERTIES	UNITS	VALUE
GENERAL		
Color	В	lack, Green, Blue
Max. continuous service temperature	°C/°F	250 / 482
Max. short-term peak temperature	°C/°F	280 / 536
Friction coefficient, typical range*		0.04 - 0.30
Food contact compliant**		Yes
* Dependent on contact pressure, sliding speed and contact geometry.		

#### **AVAILABILITY**

TriboShield coatings are applied directly to the customer's part and are suitable for complex geometries as well as various substrates e.g. steel, stainless steel, Al, Ti, Mg, etc. They can be used for both interacting surfaces that are in relative motion.


#### TYPICAL APPLICATIONS

- Pumps
- Hydraulic motors
- Precision linear guides

#### TRIBOMATE® UPGRADE AVAILABLE

Yes

### TriboShield® Standard Product Range

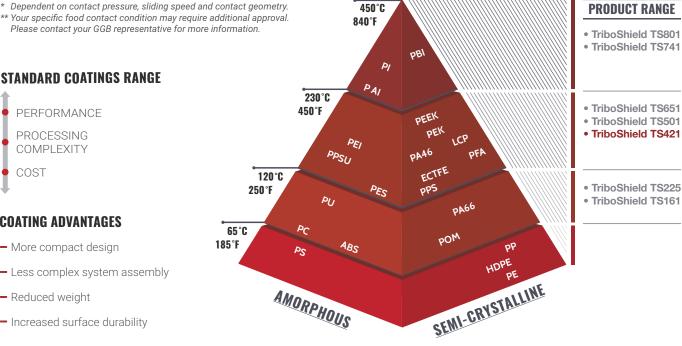

### STANDARD COATINGS RANGE

PERFORMANCE **PROCESSING** COMPLEXITY COST

- More compact design
- Less complex system assembly
- Reduced weight
- Increased surface durability

# TriboShield®TS651 Polymer Coating



### HIGH PERFORMANCE LOW-FRICTION COATING

TS651 is based on high-performance thermoplastics specifically designed for constant low-friction from low to moderately high loads in dry or lubricated conditions. Highly suitable for high-frequency/ low amplitude (HFLA) applications, particularly in dry conditions. TS651 is part of the standard TriboShield® product range.

#### **UNIQUE CHARACTERISTICS**

- Excellent performance in dry
- Good performance in lubricated condition
- Very low stick-slip characteristic
- Excellent wear resistance up to moderately high loads

BEARING PROPERTIES	UNITS	VALUE
GENERAL		
Color		Dark Brown
Max. continuous service temperature	°C/°F	260 / 500
Max. short-term peak temperature	°C/°F	280 / 536
Friction coefficient, typical range*		0.06 - 0.30
Food contact compliant**		Yes
Dependent on contact pressure, sliding speed * Your specific food contact condition may requ Please contact your GGB representative for m	uire additiona	l approval.
STANDARD COATINGS RANGE		

### AVAILABILITY TriboShield coa

TriboShield coatings are applied directly to the customer's part and are suitable for complex geometries as well as various substrates e.g. steel, stainless steel, Al, Ti, Mg, etc. They can be used for both interacting surfaces that are in relative motion.


#### TYPICAL APPLICATIONS

- Solenoid armatures
- Seat mechanisms, struts and shock absorbers...
- Compressors and radial piston pumps
- Hydraulic pumps and motors

#### TRIBOMATE® UPGRADE AVAILABLE

Yes

### TriboShield® Standard Product Range

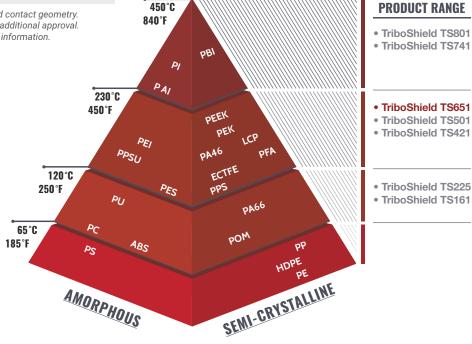

#### **COATING ADVANTAGES**

PERFORMANCE

PROCESSING COMPLEXITY

COST

- More compact design
- Less complex system assembly
- Reduced weight
- Increased surface durability

# TriboShield®TS741 Polymer Coating



### LOW-FRICTION COATING FOR HIGH LOADS APPLICATIONS

TS741 is based on high-performance thermoplastics specifically developed for demanding and heavy duty applications. Very high load bearing capacity and low-friction at moderate to high loads are some of its standout features. TS741 is part of the standard TriboShield® product range.

#### **UNIQUE CHARACTERISTICS**

- Very high load bearing capacity
- Excellent wear resistance and sliding properties
- Very low-friction in medium to high load conditions
- Very good non-stick properties

BEARING PROPERTIES	UNITS	VALUE
GENERAL		
Color		Black
Max. continuous service temperature	°C/°F	260 / 500
Max. short-term peak temperature	°C/°F	270 / 518
Friction coefficient, typical range*		0.04 - 0.25
Food contact compliant**		No
Please contact your GGB representative for m	ore imorrial	
PERFORMANCE		230 450°I
PROCESSING COMPLEXITY		
COST		120°C

#### **AVAILABILITY**

TriboShield coatings are applied directly to the customer's part and are suitable for complex geometries as well as various substrates e.g. steel, stainless steel, Al, Ti, Mg, etc. They can be used for both interacting surfaces that are in relative motion.


#### TYPICAL APPLICATIONS

- Highly loaded mechanisms
- Mechanisms requiring lifetime lubrication in dry conditions
- Submerged parts requiring corrosion protection
- Harsh chemical environments
- Braking systems, cutting blades...

#### TRIBOMATE® UPGRADE AVAILABLE

Yes

### TriboShield® Standard Product Range

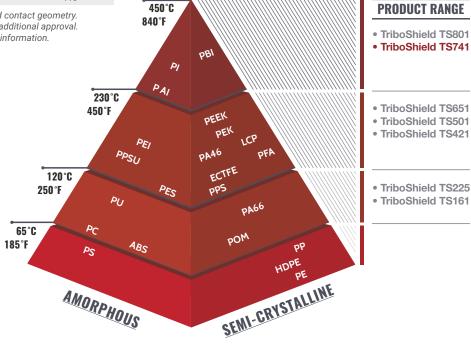

- More compact design
- Less complex system assembly
- Reduced weight
- Increased surface durability

# DP4® Bearing Material



### METAL-POLYMER ANTI-FRICTION PLAIN BEARINGS

#### **CHARACTERISTICS**

- DP4 anti-friction bushings offer good wear and low-friction performance over a wide range of loads, speeds and temperatures in dry running conditions
- Very good performance in lubricated applications
- Good performance in greased applications
- Suitable for linear, oscillating and rotating movements
- Lead-free material compliant to ELV, WEEE, and RoHS specifications
- Approved to standard DIN EN 1797: 2002-02 and ISO 21010: 2004-04 (Cryogenic Vessels – Gas/Material Compatibility) for piping, valves, fittings and other components in both gaseous and liquid oxygen for up to maximum temperature of 60°C and oxygen pressure of 25 bars. Contact GGB for further details.



#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:

- Cylindrical bushesFlanged bushesFlanged washers
- Sliding platesThrust washers

**Bearing forms made-to-order:** Standard forms in special dimensions, half-bearings, special shapes obtained by stamping or deep drawing, bearings with locating notches, lubricant holes and machined/stamped grooves, customized bearing designs

#### **APPLICATIONS**

**Automotive:** Braking systems, clutches, gearbox and transmissions, hinges: door, bonnet, boot, cabriolet roof tops, pedals; pumps: axial piston, radial piston, gear and vane; seat mechanisms, steering systems, struts and shock absorbers, wiper systems, etc.

**Industrial:** Aerospace, agricultural equipment, construction equipment, food and beverage, material handling equipment, formingmachines: metal, plastic and rubber; office equipment, medical and scientific equipment, packaging equipment, pneumatic and hydraulic cylinders, pumps and motors, railroad and tramways, textile machinery, valves, etc.



OPERATING PERFORMANCE	
Dry	Good
Oil lubricated	Very good
Grease lubricated	Good
Water lubricated	Fair
Process fluid lubricated	Good

FOR SUPERIOR PEFORMANCE	
Water lubricated	DP4-B

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	250 140
Operating temperature	Min Max	°C °C	-200 280
Coefficient of linear thermal expansion	Parallel to the surface Normal to the surface	10 <sup>-6</sup> /K 10 <sup>-6</sup> /K	11 30
DRY			
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,0
Coefficient of friction, f			0,04 - 0,25*
OIL LUBRICATED			
Maximum sliding speed, U		m/s	5,0
Maximum pU factor		N/mm <sup>2</sup> x m/s	10,0
Coefficient of friction, f			0,02 - 0,08
RECOMMENDATIONS			
Shaft surface roughness, Ra	Dry Lubricated	μm μm	0,3 - 0,5 ≤ 0,05 - 0,4*
Shaft surface hardness	Unhardened acceptable, improved bearing life	НВ	> 200

<sup>\*</sup> Depending on operating conditions

# DP4-B Bearing Material





#### **CHARACTERISTICS**

- Good wear and low-friction performance over a wide range of loads, speeds and temperatures in dry running conditions
- Very good performance in lubricated applications
- Good performance in greased applications
- Suitable for linear, oscillating and rotating movements
- Bronze back offers improved corrosion-resistance in humid/saline environments
- Lead-free material



#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:

Cylindrical bushesFlanged bushesSliding plates

**Bearing forms made-to-order:** Standard forms in special dimensions, thrust washers, flanged-thrust washers, halfbearings, special shapes obtained by stamping or deep drawing, bearings with locating notches, lubricant holes and machined / stamped grooves

#### **APPLICATIONS**

**Industrial:** Aerospace, agricultural equipment, construction equipment, material handling equipment, forming machines - metal, plastic and rubber; office equipment, medical and scientific equipment, packaging equipment, pneumatic and hydraulic cylinders, pumps and motors, railroad and tramways, textile machinery, valves, etc.

**Others:** Civil engineering, marine and offshore equipment, other applications in water or in outdoor environments, etc.



OPERATING PERFORMANCE	
Dry	Good
Oil lubricated	Very good
Grease lubricated	Good
Water lubricated	Good
Process fluid lubricated	Good

FOR SUPERIOR PEFORMANCE	
Water lubricated	DP4-B

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	140 140
Operating temperature	Min Max	°C °C	-200 280
Coefficient of linear thermal expansion	Parallel to the surface Normal to the surface	10 <sup>-6</sup> /K 10 <sup>-6</sup> /K	18 36
DRY			
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,0
Coefficient of friction, f			0,02 - 0,25*
OIL LUBRICATED			
Maximum sliding speed, U		m/s	5,0
Maximum pU factor		N/mm <sup>2</sup> x m/s	10,0
Coefficient of friction, f			0,02 - 0,08*
RECOMMENDATIONS			
Shaft surface roughness, Ra	Dry Lubricated	μm μm	0,3 - 0,5 ≤ 0,05 - 0,4*
Shaft surface hardness	Unhardened acceptable, improved bearing life	НВ	> 200

<sup>\*</sup> Depending on operating conditions

# DU® Bearing Material

# 989

### METAL-POLYMER ANTI-FRICTION PLAIN BEARINGS

#### **CHARACTERISTICS**

- Very good wear and low-friction performance over a wide range of loads, speeds and temperatures in dry running conditions
- Suitable for lubricated applications
- Suitable for linear, oscillating and rotating movements

#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:

- Cylindrical bushes Flanged bushes Flanged washers
- Sliding platesThrust washers

**Bearing forms made-to-order:** Standard forms in special dimensions, half-bearings, special shapes obtained by stamping or deep drawing, customized bearing designs

#### **APPLICATIONS**

**Industrial:** Aerospace, agricultural equipment, construction equipment, food and beverage, material handling equipment, forming machines: metal, plastic and rubber; office equipment, medical and scientific equipment, packaging equipment, pneumatic and hydraulic cylinders, pumps and motors, railroad and tramways, textile machinery, valves, etc.



OPERATING PERFORMANCE	
Dry	Very good
Oil lubricated	Good
Grease lubricated	Fair
Water lubricated	Fair
Process fluid lubricated	Fair

FOR SUPERIOR / LEAD-FREE PEFORMANCE			
Dry	DP4 / DP11		
Oil lubricated	DP4 / DP31		
Grease lubricated	DP4 / DX		
Water lubricated	DP4-B		
Process fluid lubricated	DP4 /DP31		

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	250 140
Operating temperature	Min Max	°C	-200 280
Coefficient of linear thermal expansion	Parallel to the surface Normal to the surface	10 <sup>-6</sup> /K 10 <sup>-6</sup> /K	11 30
DRY			
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,8
Coefficient of friction, f			0,02 - 0,25*
OIL LUBRICATED			
Maximum sliding speed, U		m/s	5,0
Maximum pU factor		N/mm <sup>2</sup> x m/s	5,0
Coefficient of friction, f			0,02 - 0,12
RECOMMENDATIONS			
Shaft surface roughness, Ra	Dry Lubricated	μm μm	0,3 - 0,5 ≤ 0,05 - 0,4*
Shaft surface hardness	Unhardened acceptable, improved bearing life	НВ	> 200

<sup>\*</sup> Depending on operating conditions

# DU-B Bearing Material



### METAL-POLYMER BRONZE BACKED PTFE PLAIN BEARINGS

#### **CHARACTERISTICS**

- Very good wear and low-friction performance over a wide range of loads, speeds and temperatures in dry running conditions
- Suitable for lubricated applications
- Suitable for linear, oscillating and rotating movements
- Bronze back offers improved corrosion-resistance in humid/saline environments
- Approved to standard EN1337-2 for structural bearings for civil engineering

#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:


Cylindrical bushesFlanged bushesSliding plates

**Bearing forms made-to-order:** Standard forms in special dimensions, thrust washers, flanged-thrust washers, half-bearings, special shapes obtained by stamping or deep drawing, customized bearing designs

#### **APPLICATIONS**

**Industrial:** Aerospace, agricultural equipment, construction equipment, material handling equipment, forming machines -metal, plastic and rubber; office equipment, medical and scientific equipment, packaging equipment, pneumatic and hydraulic cylinders, pumps and motors, railroad and tramways, textile machinery, valves, etc.

**Others:** Marine and offshore equipment, other applications in water or in outdoor environments



OPERATING PERFORMANCE	
Dry	Very good
Oil lubricated	Good
Grease lubricated	Fair
Water lubricated	Good
Process fluid lubricated	Fair

FOR SUPERIOR / LEAD-FREE PEFORMANCE		
Dry	DP4-B	
Oil lubricated	DP4-B	
Grease lubricated	DP4-B	
Water lubricated	DP4-B	
Process fluid lubricated	DP4-B	

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	140 140
Operating temperature	Min Max	°C	-200 280
Coefficient of linear thermal expansion	Parallel to the surface Normal to the surface	10 <sup>-6</sup> /K 10 <sup>-6</sup> /K	18 36
DRY			
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,8
Coefficient of friction, f			0,02 - 0,25*
OIL LUBRICATED			
Maximum sliding speed, U		m/s	5,0
Maximum pU factor		N/mm <sup>2</sup> x m/s	5,0
Coefficient of friction, f			0,02 - 0,12
RECOMMENDATIONS			
Shaft surface roughness, Ra	Dry Lubricated	μm μm	0,3 - 0,5 ≤ 0,05 - 0,4*
Shaft surface hardness	Unhardened acceptable, improved bearing life	НВ	> 200

<sup>\*</sup> Depending on operating conditions

# DP10 Bearing Material



#### **METAL-POLYMER ANTI-FRICTION PLAIN BEARINGS**

#### **CHARACTERISTICS**

- Good wear and low-friction performance over a wide range of loads, speeds and temperatures in dry running conditions
- Very good performance in lubricated applications particularly in marginally lubricated applications
- Suitable for linear, oscillating and rotating movements
- Lead-free material compliant to ELV, WEEE, and RoHS specifications









#### **AVAILABILITY**

- Sliding plates

#### Bearing forms available in standard dimensions:

- Cylindrical bushes - Flanged bushes
- Bearing forms made-to-order: Standard forms in special

- Thrust washers

dimensions, half-bearings, special shapes obtained by stamping or deep drawing, bearings with local notches, lubricant holes and machined/stamped grooves, customized bearing designs

#### **APPLICATIONS**

Automotive: Braking systems, clutches, hinges - door, bonnet, boot, cabriolet roof tops, pedals, pumps - axial, piston, gear, vane, seat mechanisms, steering systems, struts and shock absorbers, wiper systems, etc.

Industrial: Agricultural equipment, compressors - scroll and reciprocating, construction equipment, food and beverage, material handling equipment, forming machines - metal, plastic and rubber, office equipment, medical and scientific equipment, packaging equipment, pneumatic and hydraulic cylinders, pumps and motors, railroad and tramways, textile machinery, valves, etc.



	PTFE + Solid Lubricant
_	Porous Bronze Sinter
L	Steel Backing

OPERATING PERFO	RMANCE	
Dry		Good
Oil lubricated		Good
Grease lubricated	ı	Fair
Water lubricated	Not recon	nmended
Process fluid lubi	ricated	Fair

FOR SUPERIOR PEFORMANCE		
Grease lubricated	DP4 / DX	
Water lubricated	DP4-B	
Process fluid lubricated	DP4 / DP31	

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	250 140
Operating temperature	Min Max	°C	-200 280
Coefficient of linear thermal expansion	Parallel to the surface Normal to the surface	10 <sup>-6</sup> /K 10 <sup>-6</sup> /K	11 30
DRY			
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,0
Coefficient of friction, f			0,03 - 0,25*
OIL LUBRICATED			
Maximum sliding speed, U		m/s	5,0
Maximum pU factor		N/mm <sup>2</sup> x m/s	10,0
Coefficient of friction, f			0,02 - 0,08
RECOMMENDATIONS			
Shaft surface roughness, Ra	Dry Lubricated	μm μm	0,3 - 0,5 ≤ 0,05 - 0,4*
Shaft surface hardness	Unhardened acceptable, improved bearing life	НВ	> 200

<sup>\*</sup> Depending on operating conditions

# DP11 Bearing Material





#### **CHARACTERISTICS**

- Very good wear and low-friction performance over a wide range of loads, speeds and temperatures in dry running conditions
- Particularly suited to dry applications with high frequency and low amplitude oscillating movements
- Suitable for linear, oscillating and rotating movements
- Lead-free material compliant to ELV, WEEE, and RoHS specifications
- Approved to standard FMVSS 302 Federal Motor Vehicle Safety Standard concerning the flammability of materials used in the occupant compartments of motor vehicles








#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes, flanged bushes, thrust washers, flanged-thrust washers, sliding plates, half-bearings, special shapes obtained by stamping or deep drawing, customized bearing designs

#### **APPLICATIONS**

**Automotive:** Belt tensioners, clutches, dual mass fly-wheels, pulley dampers, etc.

**Industrial:** Applications with high frequency and low amplitude oscillating movements



OPERATING PERFORMANCE		
Dry	Very good	
Oil lubricated	Good	
Grease lubricated	l Fair	
Water lubricated	Not recommended	
Process fluid lubi	ricated Fair	

FOR SUPERIOR PEFORMANCE			
Grease lubricated	DP4 / DX		
Water lubricated DP4			
Process fluid lubricated	DP4 / DP31		

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	250 140
Operating temperature	Min Max	°C	-200 280
Coefficient of linear thermal expansion	Parallel to the surface Normal to the surface	10 <sup>-6</sup> /K 10 <sup>-6</sup> /K	11 30
DRY			
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,0
Coefficient of friction, f			0,04 - 0,25*
OIL LUBRICATED			
Maximum sliding speed, U		m/s	5,0
Maximum pU factor		N/mm <sup>2</sup> x m/s	10,0
Coefficient of friction, f			0,02 - 0,08
RECOMMENDATIONS			
Shaft surface roughness, Ra	Dry Lubricated	μm μm	0,3 - 0,5 ≤ 0,05 - 0,4*
Shaft surface hardness	Unhardened acceptable, improved bearing life	НВ	> 200

<sup>\*</sup> Depending on operating conditions

# DP31 Bearing Material



### METAL-POLYMER HYDRODYNAMIC COMPOSITE BEARINGS

#### **CHARACTERISTICS**

- Excellent low-friction and wear resistance performance in lubricated applications
- Excellent flow erosion and cavitation resistance
- Very good fatigue strength
- Lead-free material compliant to ELV, WEEE, and RoHS specifications




#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes, flanged bushes, thrust washers, flanged-thrust washers, sliding plates, half-bearings, bearings with locating notches, lubricant holes and machined/stamped grooves, customized bearing designs

#### **APPLICATIONS**

**Automotive:** Air conditioning compressors, gearbox and transmissions, heavy duty struts and shock absorbers, high performance pumps: axial piston, radial piston, gear, vane, etc.

**Industrial:** Compressors: scroll and reciprocating; pneumatic and hydraulic cylinders, high performance pumps axial piston, radial piston, gear, vane, etc.



OPERATING PERFORMANCE		
Dry	Fair	
Oil lubricated	Very good	
Grease lubricated	Fair	
Water lubricated	Fair	
Process fluid lubricated	Good	

FOR SUPERIOR PEFORMANCE		
Dry DP4 / DP11		
Grease lubricated DP4 / DX		
Water lubricated DP4-		

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	250 140
Operating temperature	Min Max	°C	-200 280
Coefficient of linear thermal expansion	Parallel to the surface Normal to the surface	10 <sup>-6</sup> /K 10 <sup>-6</sup> /K	11 30
OIL LUBRICATED			
Maximum sliding speed, U		m/s	10,0
Maximum pU factor		N/mm <sup>2</sup> x m/s	10,0
Coefficient of friction, f			0,01 - 0,05
RECOMMENDATIONS			
Shaft surface roughness, Ra	<b>a</b> Lubricated	μm	≤ 0,05 - 0,4*
Shaft surface hardness	Unhardened acceptable,	НВ	> 200

<sup>\*</sup> Depending on operating conditions

# DX® Bearing Material



### METAL-POLYMER PLAIN BEARINGS GREASE LUBRICATED

#### **CHARACTERISTICS**

- Marginally lubricated bearing material for grease or oil lubricated applications
- Standard parts contain grease indents in the sliding layer; plain sliding layer available by request
- Optimum performance under relatively high loads and low speeds
- Suitable for linear, oscillating and rotating movements
- Wide range of parts available from stock



#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:

- Cylindrical bushes - Thrust washers - Sliding plates


**Bearing forms made-to-order:** Standard forms in special dimensions, half-bearings, special shapes obtained by stamping, bearings with locating notches, lubricant holes and machined grooves, customized bearing designs

#### **APPLICATIONS**

**Automotive:** Steering gear, power steering, pedal bushes, seat slides, king-pin bushes, tailgate pivots, brake caliper bushes, etc.

**Industrial:** Mechanical handling and lifting equipment, machine slides, hydraulic cylinders, hydraulic motors, ski-lifts, pneumatic equipment, medical equipment, textile machinery, agricultural equipment, scientific equipment, etc.

#### MICROSECTION



Of Sliding layer
POM with or without Lubricant
Indents for
Machining
Porous Bronze
Sinter

Steel Backing

UPERATING PERFURMANCE	
Dry	Poor
Oil lubricated	Good
Grease lubricated	Very good
Water lubricated	Poor
Process fluid lubricated	Poor

#### FOR SUPERIOR PEFORMANCE

Dry GAR-MAX / HSG / GAR-FIL / MLG

Water lubricated HPM / HPF / DP4-B

Process fluid DP4 / HI-EX / GAR-FIL

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	140 140
Operating temperature	Min Max	°C	-40 130
Coefficient of linear thermal expansion	Parallel to the surface Normal to the surface	10 <sup>-6</sup> /K 10 <sup>-6</sup> /K	11 29
OIL LUBRICATED			
Maximum sliding speed, l	J	m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	2,8
Coefficient of friction, f			0,06 - 0,12
RECOMMENDATIONS			
Shaft surface roughness, I	Ra	μm	≤ 0,4
Shaft surface hardness	Unhardened acceptable, improved bearing life	HB HB	> 200 > 350

<sup>\*</sup> Depending on operating conditions

# DX®10 Bearing Material





### METAL-POLYMER PLAIN BEARINGS GREASE LUBRICATED

#### **CHARACTERISTICS**

- Perfect for heavy duty and harsh environments
- Excellent chemical resistance
- Excellent erosion resistance
- Good fatigue strength
- Good wear performance
- Can be broached for tighter tolerance
- Lead-free material compliant to ELV, RoHS and WEEE specifications

#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes, thrust washers, sliding plates, half-bearings, special shapes obtained by stamping, bearings with locating notches, lubricant holes and machined grooves, customized bearing designs


#### **APPLICATIONS**

**General:** Greased or oiled applications with high load, high temperature, and contamination; ideal for replacing bi-metal or bronze bushings to achieve improved wear performance

Automotive: King pins, oil pumps

**Industrial:** Piston pumps, agriculture equipment, construction, lift and cranes, small reciprocating bushing

#### **MICROSECTION**



Sliding layer High-Tech Polymer with Lubricant Indents Porous Bronze Sinter

Steel Backing

OPERATING PERFORMANCE	
Dry	Fair
Oil lubricated	Very good
Grease lubricated	Very good
Water lubricated	Poor
Process fluid lubricated	Fair

FOR SUPERIOR PEFORMANCE		
Dry	GAR-MAX / HSG / GAR-FIL / MLG	
Water lubricated HPM / HPF / DP4-B		
Process fluid lubricated	DP4 / HI-EX / GAR-FIL	

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	250 140
Operating temperature	Min Max	°C °C	-40 175
GREASE LUBRICATED			
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	2,8
Coefficient of friction, f			0,01 - 0,10
OIL LUBRICATED			
Maximum sliding speed, U		m/s	10,0
Maximum pU factor		N/mm <sup>2</sup> x m/s	2,8
Coefficient of friction, f			0,01 - 0,06
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,4
Shaft surface hardness	Normal For longer service life	HB HB	> 200 > 350

# HI-EX® Bearing Material





#### **CHARACTERISTICS**

**COMPOSITE BEARINGS** 

- Marginally lubricated bearing material with good wear resistance under thin film conditions
- Standard bearings supplied with indents for optimum retention and distribution of the lubricant over the sliding layer
- Available with non-indented overlay for hydrodynamic applications
- Rated for high temperature use up to 250°C / 480°F
- Suitable for use with low viscosity fluids
- Good chemical resistance
- Lead-free material compliant to ELV, RoHS and WEEE specifications




#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes, thrust washers, sliding plates, half-bearings, special shapes obtained by stamping, bearings with locating notches, lubricant holes and machined grooves, customized bearing designs

#### **APPLICATIONS**

**Automotive:** Diesel fuel pumps, heavy duty brakes, heavy duty axles **Industrial:** Hydraulic motors, axial and radial piston pumps, agricultural equipment, wind energy equipment, yaw and teeter bearings



OPERATING PERFORMANCE	
Dry	Fair
Oil lubricated	Good
Grease lubricated	Very good
Water lubricated	Good
Process fluid lubricated	Good

FOR SUPERIOR PEFORMANCE	
Dry	GAR-MAX / HSG / GAR-FIL / MLG

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	140 140
Operating temperature	Min Max	°C	-150 250
Coefficient of linear thermal expansion	Parallel to the surface Normal to the surface	10 <sup>-6</sup> /K 10 <sup>-6</sup> /K	11 29
GREASE LUBRICATED			
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	2,8
Coefficient of friction, f			0,08 - 0,12
OIL LUBRICATED			
Maximum sliding speed, U		m/s	10,0
Maximum pU factor		N/mm <sup>2</sup> x m/s	10,0
Coefficient of friction, f			0,03 - 0,08
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,05 - 0,4*
Shaft surface hardness	Normal For longer service life	HB HB	> 200 > 350

<sup>\*</sup> Depending on operating conditions

# DTS10<sup>®</sup> Bearing Material









#### **METAL-POLYMER HYDRONAMIC COMPOSITE BEARINGS**

#### **CHARACTERISTICS**

- The first polymer-lined bearing for lubricated conditions offering low-friction and high wear resistance that is designed to be machined on-site for tight tolerances
- Excellent wear resistance and low-friction in lubricated hydraulic applications
- Excellent chemical resistance, fatigue strength, cavitation and flow erosion resistance, and good behavior in dry start-up conditions
- A minimum overlay thickness of 0,1 mm permits, under carefully controlled conditions, machining of the assembled bore for improved dimensional tolerance and reduced geometric defects, while retaining a thin layer of PTFE sliding surface
- Compatible with most standard machining processes including turning, broaching, reaming, and milling
- Lead-free material compliant to ELV, RoHS and WEEE specifications

#### **AVAILABILITY**

Bearing forms made-to-order: Standard forms in special dimensions, half-bearings, special shapes obtained by stamping or deep drawing, bearings with locating notches, lubricant holes and machined/stamped grooves, customized bearing designs

#### **APPLICATIONS**

Industrial: Compressors: scroll and reciprocating, external and internal motors, external and internal pumps, vane pumps, axial and radial piston pumps, gerotor pumps, hydraulic cylinders



	→ Sliding layer PTFE + Fillers
	—≀ Porous Bronze Sinter
•	— Steel Backing

OPERATING PERFORMANCE	
Dry	Fair
Oil lubricated	Excellent
Grease lubricated	Fair
Water lubricated	Fair
Process fluid lubricated	Good

FOR SUPERIOR PEFORMANCE	
Dry GAR-MAX / HSG / GAR-FIL / MLG	
Grease lubricated DX / DX10	
Water lubricated HPM / HPF / DP4-B	

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static	N/mm²	140
Operating temperature	Min Max	°C	-200 280
FLUID LUBRICATED			
Maximum sliding speed, U		m/s	10,0
Maximum pU factor		N/mm <sup>2</sup> x m/s	100*
Coefficient of friction, f			0,01 - 0,08
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,05 - 0,2*
Shaft surface hardness		НВ	> 200

<sup>\*</sup> Depending on operating conditions

# DS Bearing Material



### METAL-POLYMER SELF-LUBRICATING BEARINGS

#### **CHARACTERISTICS**

- Self-lubricating bearing material for operation in mixed film lubrication conditions
- Sliding layer is machinable (ca. 0,4 mm above bronze sinter layer)
- Resistant to fretting corrosion damage to the shaft under low amplitude oscillating movements
- Similar in performance to DX® but with lower friction




#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes, thrust washers, sliding plates, half-bearings, special shapes obtained by stamping, customized bearing designs

#### **APPLICATIONS**

**Automotive:** Steering gear, power steering, pedal bushes, seat slides, king-pin bushes, tailgate pivots, brake caliper bushes, etc. **Industrial:** Mechanical handling and lifting equipment, machine slides, hydraulic cylinders, hydraulic motors, ski lifts, pneumatic equipment, medical equipment, textile machinery, agricultural equipment, scientific equipment, etc.



OPERATING PERFORMANCE		
Dry	Good	
Oil lubricated	Very good	
Grease lubricated	Very good	
Water lubricated	Poor	
Process fluid lubricated	Poor	

FOR SUPERIOR PEFORMANCE	
Water lubricated	HPM / HPF / DP4-B
Process fluid lubricated	DP4 / GAR-FIL / HI-EX

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm <sup>2</sup> N/mm <sup>2</sup>	110 45
Operating temperature	Min Max	°C °C	-60 130
DRY			
Maximum sliding speed, U		m/s	1,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,4
Coefficient of friction, f			0,15 - 0,3
GREASE LUBRICATED			
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	2,8
Coefficient of friction, f			0,05 - 0,1
OIL LUBRICATED			
Maximum sliding speed, U		m/s	10,0
Maximum pU factor		N/mm <sup>2</sup> x m/s	10,0
Coefficient of friction, f			0,03 - 0,08
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,4
Shaft surface hardness	Normal For longer service life	HB HB	> 200 > 350

# EP® Bearing Material



### SELF-LUBRICATING ENGINEERED PLASTIC BEARINGS

#### **CHARACTERISTICS**

- Good bearing performance in dry working conditions
- Good bearing performance in lubricated or marginally lubricated applications
- Corrosion-resistant in humid/saline environments
- Very good price performance ratio
- Very good weight performance ratio
- Within injection moulding tool feasibility unlimited dimensions and design features
- Compliant to ELV, WEEE and RoHS specifications







#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:


Plain cylindrical bushesPlain flanged bushes

**Bearing forms made-to-order:** Standard forms in special dimensions, thrust washers, half-bearings, sliding plates, customized bearing designs

#### **APPLICATIONS**

**General:** Generally applicable within the limits of the material properties

**Industrial:** Medical equipment, awnings and blinds, scientific equipment, gaming equipment, office equipment, etc.



OPERATING PERFOR	MANCE
Dry	Good
Oil lubricated	Good
Grease lubricated	Good
Water lubricated	Fair
Process fluid	Good after

FOR SUPERIOR PEFORMANCE	
Water lubricated	EP22

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	80 40
Operating temperature Min Max		°C	-40 140
Coefficient of linear thermal expansion		10 <sup>-6</sup> /K	22
DRY			
Maximum sliding speed, U		m/s	1,0
Maximum pU factor	for $A_H/A_C = 5$ for $A_H/A_C = 10$ for $A_H/A_C = 20$	$N/mm^2 x m/s$ $N/mm^2 x m/s$ $N/mm^2 x m/s$	0,06 0,24 1,00
Coefficient of friction, f			0,15 - 0,3
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,2 - 0,8
Shaft surface hardness		HV	> 200

# EP®12 Bearing Material









### SELF-LUBRICATING ENGINEERED PLASTIC BEARINGS

#### **CHARACTERISTICS**

- Good bearing performance in dry working conditions
- Good bearing performance in lubricated or marginally lubricated applications
- Corrosion-resistant in humid/saline environments
- Very good price performance ratio
- Very good weight performance ratio
- Within injection moulding tool feasibility unlimited dimensions and design features
- Compliant to ELV, WEEE and RoHS specifications


#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes, flanged bearings, thrust washers, sliding plates, half-bearings, customized bearing designs

#### **APPLICATIONS**

**General:** Generally applicable within the limits of the material properties

**Industrial:** Domestic appliances, furniture, office equipment, sports equipment and many more



OPERATING PERFORMANCE	
Dry	Very good
Oil lubricated	Good
Grease lubricated	Good
Water lubricated	Fair
Process fluid lubricated	Good after resistance testing

FOR SUPERIOR PEFORMANCE	
Water lubricated	EP22

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static	N/mm²	65
Operating temperature	Min Max	°C °C	-40 125
Coefficient of linear thermal expan	sion	10 <sup>-6</sup> /K	120
DRY			
Maximum sliding speed, U		m/s	1,0
Maximum pU factor	for $A_H/A_C = 5$ for $A_H/A_C = 10$ for $A_H/A_C = 20$	N/mm² x m/s N/mm² x m/s N/mm² x m/s	0,04 0,09 0,18
Coefficient of friction, f			0,18 - 0,3
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,1 - 0,5
Shaft surface hardness		HV	> 200

# EP®15 Bearing Material



### UV-RESISTANT BEARINGS FOR SUN & OUTDOOR APPLICATIONS

#### **CHARACTERISTICS**

- UV-resistant bearings
- Abrasion-resistant
- Lightweight
- Low coefficient of friction
- Very good bushing performance in dry working conditions
- Good bushing performance in lubricated or marginally lubricated applications
- Corrosion-resistant in humid/ saline environments
- Very good price performance ratio
- Very good weight performance ratio
- Within injection molding tool feasibility unlimited dimensions and design features
- Compliant to ELV, WEEE and RoHS specifications




#### **AVAILABILITY**

**EP®15 Bearing forms made-to-order:** Cylindrical bushings, flanged bushings, thrust washers, sliding plates, half-bushings, customized bearing designs

#### **APPLICATIONS**

Solar Power Equipment, Outdoor Applications, Recreational Applications





OPERATING PERFOR	MANCE
Dry	Very good
Oil lubricated	Good
Grease lubricated	Good
Water lubricated	Fair
Process fluid lubricated	Good after resistance testing

BEARING PROPERTIES	STANDARD	UNITS	VALUE
CHARACTERISTICS			
Charpy unnotched impact strength	ISO 179/1eU	kJ/m²	45
Charpy notched impact strength	ISO 179/1eA	kJ/m²	4,5
Coefficient of linear thermal expansion	ISO 11359-2:1999-10	x10 <sup>-6</sup>	120
Minimum temperature		°C/°F	- 40 / - 40
Maximum temperature		°C / °F	125 / 260
Maximum extended temperature limit		°C/°F	125 / 260
Density	DIN EN ISO 1183-1 :2013-04 DIN EN ISO 1183-2 :2004-10	g/cm <sup>3</sup>	1,50
Tensile strength	DIN EN ISO 527-1 :2012-06 DIN EN ISO 527-2 :2012-06 DIN EN ISO 527-3 :2003-07	N/mm² / psi	50 / 7252
Elastic modulus in tension	DIN EN ISO 178:2013-09 DIN EN ISO 527-1:2012-06 DIN EN ISO 604:2003-12	N/mm² / psi	2750 / 398854
Maximum static load		N/mm² / psi	65 / 9500
Coefficient of friction, f			0,09 - 0,15
Color			Blue

# EP®22 Bearing Material





### SELF-LUBRICATING ENGINEERED PLASTIC BEARINGS

#### **CHARACTERISTICS**

- Good bearing performance in dry working conditions
- Very good bearing performance in lubricated or marginally lubricated applications
- Corrosion-resistant in humid/saline environments
- Very good price performance ratio
- Very good weight performance ratio
- Within injection moulding tool feasibility unlimited dimensions and design features
- Compliant to ELV, WEEE and RoHS specifications

#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:


Plain cylindrical bushesPlain flanged bushes

**Bearing forms made-to-order:** Standard forms in special dimensions, thrust washers, half-bearings, sliding plates, customized bearing designs

#### **APPLICATIONS**

**General:** Generally applicable within the limits of the material properties

**Industrial:** Domestic appliances, chemical equipment, office equipment, sports equipment and many more



OPERATING PERFORMANCE		
Dry	Very good	
Oil lubricated	Good	
Grease lubricated	Good	
Water lubricated	Very good	
Process fluid lubricated	Good after resistance testing	

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static	N/mm²	50
Operating temperature	Min Max	°C	-50 170
Coefficient of linear thermal expan	nsion	10 <sup>-6</sup> /K	90
DRY			
Maximum sliding speed, U		m/s	1,0
Maximum pU factor	for $A_H/A_C = 5$ for $A_H/A_C = 10$ for $A_H/A_C = 20$	N/mm² x m/s N/mm² x m/s N/mm² x m/s	0,05 0,10 0,20
Coefficient of friction, f			0,22 - 0,37
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,1 - 0,5
Shaft surface hardness		HV	> 200

# EP®30 Bearing Material





### SELF-LUBRICATING ENGINEERED PLASTIC BEARINGS

#### **CHARACTERISTICS**

- Good bearing performance in dry working conditions
- Very good bearing performance in lubricated or marginally lubricated applications
- Corrosion-resistant in humid/saline environments
- Very good price performance ratio
- Very good weight performance ratio
- Very good in elasto hydrodynamic applications
- Within injection moulding tool feasibility unlimited dimensions and design features
- Compliant to ELV, WEEE and RoHS specifications

#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:

Plain cylindrical bushes
 Plain flanged bushes

**Bearing forms made-to-order:** Standard forms in special dimensions, thrust washers, half-bearings, sliding plates, customized bearing designs

#### **APPLICATIONS**

**General:** Generally applicable within the limits of the material properties

**Industrial:** Domestic appliances, chemical equipment, office equipment, sports equipment and many more



OPERATING PERFORMANCE		
Dry	Very good	
Oil lubricated	Good	
Grease lubricated	Good	
Water lubricated	Very good	
Process fluid lubricated	Good after resistance testing	

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static	N/mm <sup>2</sup>	65
Operating temperature	Min Max	°C	-50 200
Coefficient of linear thermal expansion		10 <sup>-6</sup> /K	40
DRY			
Maximum sliding speed, U		m/s	1,0
Maximum pU factor	for $A_H/A_C = 5$ for $A_H/A_C = 10$ for $A_H/A_C = 20$	$N/mm^2 x m/s$ $N/mm^2 x m/s$ $N/mm^2 x m/s$	0,05 0,10 0,20
Coefficient of friction, f			0,08 - 0,16
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,1 - 0,5
Shaft surface hardness		HV	> 200

# EP®43 Bearing Material









### SELF-LUBRICATING ENGINEERED PLASTIC BEARINGS

#### **CHARACTERISTICS**

- Good bearing performance in dry working conditions
- Good bearing performance in lubricated or marginally lubricated applications
- Corrosion-resistant in humid/saline environments
- Very good price performance ratio for high temperature applications
- Very good weight performance ratio
- Within injection moulding tool feasibility unlimited dimensions and design features
- Compliant to ELV, WEEE and RoHS specifications

#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:


Plain cylindrical bushesPlain flanged bushes

**Bearing forms made-to-order:** Standard forms in special dimensions, thrust washers, half-bearings, sliding plates, customized bearing designs

#### **APPLICATIONS**

**General:** Generally applicable within the limits of the material properties

**Industrial:** Domestic appliances, materials handling equipment, apparatus engineering, slot machines and cash boxes and many more



OPERATING PERFOR	MANCE
Dry	Very good
Oil lubricated	Good
Grease lubricated	Good
Water lubricated	Very good
Process fluid lubricated	Good after resistance testing

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static	N/mm²	83
Operating temperature	Min Max	°C	-40 240
Coefficient of linear thermal expansion		10 <sup>-6</sup> /K	45
DRY			
Maximum sliding speed, U		m/s	1,0
Maximum pU factor	for $A_H/A_C = 5$ for $A_H/A_C = 10$ for $A_H/A_C = 20$	N/mm² x m/s N/mm² x m/s N/mm² x m/s	0,22 0,90 3,59
Coefficient of friction, f			0,11 - 0,2
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,2 - 0,8
Shaft surface hardness		HV	> 200

# EP®44 Bearing Material





### SELF-LUBRICATING ENGINEERED PLASTIC BEARINGS

#### **CHARACTERISTICS**

- Good bearing performance in dry working conditions
- Good bearing performance in lubricated or marginally lubricated applications
- Corrosion-resistant in humid/saline environments
- Very good price performance ratio for high temperature applications
- Very good weight performance ratio
- Within injection moulding tool feasibility unlimited dimensions and design features
- Compliant to ELV, WEEE and RoHS specifications

#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes, thrust washers, sliding plates, half-bearings, special shapes obtained by stamping, bearings with locating notches, lubricant holes and machined grooves, customized bearing designs

#### **APPLICATIONS**

**General:** Generally applicable within the limits of the material properties

**Industrial:** Domestic appliances, valve technology, electronics assembly, apparatus engineering and many more



OPERATING PERFOR	RMANCE
Dry	Good
Oil lubricated	Very Good
Grease lubricated	Very Good
Water lubricated	Very Good
Process fluid lubricated	Good after resistance testing

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static	N/mm <sup>2</sup>	95
Operating temperature	Min Max	°C	-40 240
Coefficient of linear thermal expansion		10 <sup>-6</sup> /K	27
DRY			
Maximum sliding speed, U		m/s	1,0
Maximum pU factor	for $A_H/A_C = 5$ for $A_H/A_C = 10$ for $A_H/A_C = 20$	N/mm² x m/s N/mm² x m/s N/mm² x m/s	0,11 0,42 1,69
Coefficient of friction, f			0,16 - 0,26
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,2 - 0,8
Shaft surface hardness		HV	> 450

# EP®63 Bearing Material







#### **SELF-LUBRICATING ENGINEERED PLASTIC BEARINGS**

#### **CHARACTERISTICS**

- Good bearing performance in dry working conditions
- Good bearing performance in lubricated or marginally lubricated applications
- Corrosion-resistant in humid/saline environments
- Suitable for very high temperature applications
- Very good weight performance ratio
- Within injection moulding tool feasibility unlimited dimensions and design features
- Compliant to ELV, WEEE and RoHS specifications

#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:

Plain cylindrical bushesPlain flanged bushes

Bearing forms made-to-order: Standard forms in special dimensions, thrust washers, half-bearings, sliding plates, customized bearing designs

#### **APPLICATIONS**

**General:** Generally applicable within the limits of the material properties

Industrial: Domestic appliances, valve technology, electronics assembly, agricultural machinery and many more



RMANCE
Good
Good
Good
Fair
Good after resistance testing

FOR SUPERIOR PEFORMANCE	
Water lubricated	EP64

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static	N/mm <sup>2</sup>	90
Operating temperature	Min Max	°C °C	-100 290
Coefficient of linear thermal expan	nsion	10 <sup>-6</sup> /K	50
DRY			
Maximum sliding speed, U		m/s	1,0
Maximum pU factor	for $A_H/A_C = 5$ for $A_H/A_C = 10$ for $A_H/A_C = 20$	N/mm² x m/s N/mm² x m/s N/mm² x m/s	0,16 0,66 2,63
Coefficient of friction, f			0,12 - 0,21
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,1 - 0,5
Shaft surface hardness		HV	> 200

# EP®64 Bearing Material





### SELF-LUBRICATING ENGINEERED PLASTIC BEARINGS

#### **CHARACTERISTICS**

- Good bearing performance in lubricated or marginally lubricated applications
- Excellent flow erosion and cavitation resistance
- Corrosion-resistant in humid/saline environments
- Suitable for very high temperature applications
- Very good weight performance ratio
- Within injection moulding tool feasibility unlimited dimensions and design features
- Compliant to ELV, WEEE and RoHS specifications


#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes, flanged bearings, thrust washers, sliding plates, half-bearings, customized bearing designs

#### **APPLICATIONS**

**General:** Generally applicable within the limits of the material properties

**Industrial:** Domestic appliances, transportation equipment, apparatus engineering, conveyor equipment and many more



OPERATING PERFOR	RMANCE
Dry	Good
Oil lubricated	Very good
Grease lubricated	Very good
Water lubricated	Good
Process fluid lubricated	Good after resistance testing

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static	N/mm²	125
Operating temperature	Min Max	°C °C	-100 290
Coefficient of linear thermal expansion		10 <sup>-6</sup> /K	14
DRY			
Maximum sliding speed, U		m/s	1,0
Maximum pU factor	for $A_H/A_C = 5$ for $A_H/A_C = 10$ for $A_H/A_C = 20$	N/mm² x m/s N/mm² x m/s N/mm² x m/s	0,09 0,35 1,40
Coefficient of friction, f			0,3 - 0,5
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,1 - 0,5
Shaft surface hardness		HV	> 450

# EP®73 Bearing Material









#### **SELF-LUBRICATING ENGINEERED PLASTIC BEARINGS**

#### **CHARACTERISTICS**

- Good bearing performance in dry working conditions
- Good bearing performance in lubricated or marginally lubricated applications
- Corrosion-resistant in humid/saline environments
- Very good dimensional stability
- Very good weight performance ratio
- Within injection moulding tool feasibility unlimited dimensions and design features
- Compliant to ELV, WEEE and RoHS specifications

#### **AVAILABILITY**

Bearing forms made-to-order: Cylindrical bushes, flanged bearings, thrust washers, sliding plates, half-bearings, customized bearing designs


#### **APPLICATIONS**

General: Generally applicable within the limits of the material properties

Automotive: Automatic gears, pumps, sealing in turbo compressors, piston rings, valve seats, sealings

**Industrial:** Continuous furnaces, drying furnaces for coating, textile machines and many more

Aerospace: Weight saving by replacement of aluminum or metal alloys, while providing superior stability and viscosity. Applicable in extreme high and low temperatures e.g. turbojet engine compressor blade



 PAI + Solid Lubricant + Fillers

OPERATING PERFORMANCE				
Good				
Good				
Good				
Fair				
Good after resistance testing				

FOR SUPERIOR PEFORMANCE	
Water lubricated	EP64

BEARING PROPERTIES		UNITS	VALUE	
GENERAL				
Maximum load, p	Static	N/mm <sup>2</sup>	105	
Operating temperature	Min Max	°C	-200 260	
Coefficient of linear thermal expansion		10 <sup>-6</sup> /K	25	
DRY				
Maximum sliding speed, U		m/s	2,5	
Maximum pU factor	for $A_H/A_C = 5$ for $A_H/A_C = 10$ for $A_H/A_C = 20$	$N/mm^2 x m/s$ $N/mm^2 x m/s$ $N/mm^2 x m/s$	0,10 0,39 1,57	
Coefficient of friction, f			0,19 - 0,31	
LUBRICATED				
Maximum sliding speed, U		m/s	5,0	
RECOMMENDATIONS				
Shaft surface roughness, Ra		μm	0,2 - 0,8	
Shaft surface hardness		HV	> 200	

# EP®79 Bearing Material







#### **SELF-LUBRICATING ENGINEERED PLASTIC BEARINGS**

#### **CHARACTERISTICS**

- Excellent flow erosion and cavitation resistance
- Excellent performance in fully lubricated applications
- Corrosion-resistant in humid/saline environments
- Excellent dimensional stability
- Very good weight performance ratio
- Within injection moulding tool feasibility unlimited dimensions and design features
- Compliant to ELV, WEEE and RoHS specifications

#### **AVAILABILITY**


Bearing forms made-to-order: Cylindrical bushes, flanged bearings, thrust washers, sliding plates, half-bearings, customized bearing designs

#### **APPLICATIONS**

General: Generally applicable within the limits of the material

**Automotive:** Automatic gears

Industrial: Domestic appliances, control valves, fittings, textile machines and many more



OPERATING PERFORMANCE				
Dry	Not recommended			
Oil lubricated	Very good			
Grease lubricated	Very good			
Water lubricated	Fair			
Process fluid lubricated	Good after resistance testing			

FOR SUPERIOR PEFORMANCE	
Dry	EP73
Water lubricated	EP64

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static	N/mm <sup>2</sup>	130
Operating temperature	Min Max	°C	-200 260
Coefficient of linear thermal expansion		10 <sup>-6</sup> /K	9
DRY			
Maximum sliding speed, U		m/s	10,0
Maximum pU factor		N/mm <sup>2</sup> x m/s	10,0
Coefficient of friction, f			0,005 - 0,1
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,2 - 0,8
Shaft surface hardness		HV	> 500

# KA Glacetal Bearing Material



### ENGINEERED PLASTIC THRUST WASHERS

#### **CHARACTERISTICS**

- Good bearing performance in light duty working conditions
- Good performance in lubricated or marginally lubricated applications
- Corrosion-resistant in humid/saline environments
- Very good price performance ratio
- Very good weight performance ratio



#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:

- Plain thrust washers

Non standard parts made-to-order

#### **APPLICATIONS**

**Industrial:** Thrust washers are used as axial bearings in conjunction with all cylindrical bushes according to ISO 3547 to prevent metal-to-metal contact and fretting damage



OPERATING PERFORMANCE	
Dry	Fair
Oil lubricated	Good
Grease lubricated	Good
Water lubricated	Fair
Process fluid lubricated	Fair

FOR SUPERIOR PEFORMANCE		
Dry	EP22	
Water lubricated	EP22	
Process fluid lubricated	EP22	

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	20 10
Operating temperature	Min Max	°C °C	-40 80
GREASED			
Maximum sliding speed, U		m/s	1,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	0,35
Coefficient of friction, f			0,08 - 0,12
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,4
Shaft surface hardness	Normal For longer service life	HB HB	> 200 > 350

# Multilube Bearing Material



### THERMOPLASTIC PLAIN BEARINGS

#### **CHARACTERISTICS**

- Good bearing performance in dry working conditions
- Good performance in lubricated or marginally lubricated applications
- Corrosion-resistant in humid/saline environments
- Good price performance ratio
- Very good weight performance ratio
- Within injection moulding tool feasibility unlimited dimensions and design features






#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes, flanged bearings, thrust washers, sliding plates, half-bearings, customized bearing designs

#### **APPLICATIONS**

Industrial: Linkages, seat suspensions



OPERATING PERFORMANCE	
Dry	Good
Oil lubricated	Good
Grease lubricated	Good
Water lubricated	Fair
Process fluid lubricated	Fair

FOR SUPERIOR PEFORMANCE	
Water lubricated	EP22
Process fluid lubricated	EP22

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	60 30
Operating temperature Min Max Momentary		°C °C	-40 80 120
Coefficient of linear thermal expansion		10 <sup>-6</sup> /K	101
DRY			
Maximum sliding speed, U		m/s	1,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	0,6
Coefficient of friction, f			0,1 - 0,2
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,2 - 0,8
Shaft surface hardness	Normal For longer service life	HB HB	> 200 > 350

# GAR-MAX® Bearing Material



### SELF-LUBRICATING FIBERGLASS REINFORCED PLAIN BEARINGS

#### **CHARACTERISTICS**

- High load capacity
- Excellent shock and misalignment resistance
- Excellent contamination resistance
- Very good friction and wear properties
- Good chemical resistance
- Very good dry wear performance
- GAR-MAX® bearing sizes available according to DIN ISO 4379 for the replacement of traditional greased bronze bearings





#### **AVAILABILITY**


#### Bearing forms available in standard dimensions:

- Plain cylindrical bushes

**Non-standard parts made-to-order:** Cylindrical bushes with non-standard lengths and wall thickness, customized bushing designs

#### **APPLICATIONS**

**Industrial:** Steering linkages, hydraulic cylinder pivots, king pin bearings, boom lifts, scissor lifts, cranes, hoists, lift gates, backhoes, trenchers, skid steer loaders, front end loaders, etc.



OPERATING PERFORMANCE		
Dry	Very good	
Oil lubricated	Fair	
Grease lubricated	Fair	
Water lubricated	Fair	
Process fluid lubricated	Poor	

FOR SUPERIOR PEFORMANCE		
Oil lubricated	GAR-FIL	
Grease lubricated	DX / DX10	
Water lubricated	HPF / HPM	
Process fluid lubricated GAR-FIL		

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm <sup>2</sup> N/mm <sup>2</sup>	210 140
Operating temperature	Min Max	°C °C	-195 160
DRY			
Maximum sliding speed, U		m/s	0,13
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,05
Coefficient of friction, f			0,05 - 0,3*
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,15 - 0,4
Shaft surface hardness	Normal For longer service life	HB HB	> 350 > 480

<sup>\*</sup> Depending on operating conditions

# GAR-FIL Bearing Material



### FIBER REINFORCED COMPOSITE BEARINGS WITH PTFE TAPE LINER

#### **CHARACTERISTICS**

- Proprietary filled PTFE tape liner
- High load capacity
- Good chemical resistance
- Machinable bearing surface
- High rotational speed capacity
- Very good friction and wear properties
- Excellent contamination resistance



#### **AVAILABILITY**


#### Bearing forms available in standard dimensions:

- Plain cylindrical bushes

**Non-standard parts made-to-order:** Cylindrical bushes with non-standard lengths and wall thickness, flanged bearings, hexagonal and square bores, liner on outer diameter, customized bearing designs

#### **APPLICATIONS**

Industrial: Valves, scissor lifts, pulleys, toggle linkages, etc.



OPERATING PERFORMANCE		
Dry	Very good	
Oil lubricated	Very good	
Grease lubricated	Fair	
Water lubricated	Fair	
Process fluid lubricated	Very good	

FOR SUPERIOR PEFORMANCE		
Grease lubricated	DX / DX10	
Water lubricated	HPF / HPM	

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	140 140
Operating temperature	Min Max	°C °C	-195 205
DRY			
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,23
Coefficient of friction, f			0,02 - 0,12*
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,4
Shaft surface hardness	Normal	НВ	> 200

<sup>\*</sup> Depending on operating conditions

# **HSG** Bearing Material



#### **HIGH-LOAD FIBER REINFORCED COMPOSITE PTFE BEARINGS**

#### **CHARACTERISTICS**

- Self-lubricating plain bearing material
- High load capacity (twice as much as standard GAR-MAX® bearings)
- Excellent shock and misalignment resistance
- Excellent contamination resistance
- Very good friction and wear properties
- Good chemical resistance







#### **AVAILABILITY**


#### Bearing forms available in standard dimensions:

- Plain cylindrical bushes

Non-standard parts made-to-order: Cylindrical bushes with non-standard lengths and wall thickness, flanged bearings, hexagonal and square bores, liner on outer diameter, customized bearing designs

#### **APPLICATIONS**

Industrial: Steering linkages, hydraulic cylinder pivots, king pin bearings, boom lifts, scissor lifts, cranes, hoists, lift gates, backhoes, trenchers, skid steer loaders, front end loaders, etc.



OPERATING PERFORMANCE	
Dry	Very good
Oil lubricated	Fair
Grease lubricated	Fair
Water lubricated	Fair
Process fluid lubricated	Fair

FOR SUPERIOR PEFORMANCE			
Oil lubricated GAR-FIL			
Grease lubricated DX / DX10			
Water lubricated HPF / HPM			
Process fluid lubricated GAR-FIL			

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	415 140
Operating temperature	Min Max	°C °C	-195 160
DRY			
Maximum sliding speed, U		m/s	0,13
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,05
Coefficient of friction, f			0,05 - 0,3*
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,15 - 0,4
Shaft surface hardness	Normal For longer service life	HB HB	> 350 > 480

<sup>\*</sup> Depending on operating conditions

## MLG Bearing Material



### SELF-LUBRICATING FIBER REINFORCED COMPOSITE BEARINGS

#### **CHARACTERISTICS**

- Value engineered filament-wound bearing for lighter duty applications
- High load capacity
- Good misaligment resistance
- Excellent shock resistance
- Good friction and wear properties
- Good chemical resistance



#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes with non-standard lengths and wall thickness, flanged bearings, hexagonal and square bores, liner on outer diameter, customized bearing designs

#### **APPLICATIONS**

**Industrial:** Construction and earth moving equipment, conveyors, cranes, hoists, hydraulic cylinder pivots, etc.



OPERATING PERFORMANCE		
Dry	Very good	
Oil lubricated	Good	
Grease lubricated	Poor	
Water lubricated	Fair	
Process fluid lubricated	Fair	

FOR SUPERIOR PEFORMANCE			
Grease lubricated	DX / DX10		
Water lubricated HPF / HPM			
Process fluid lubricated GAR-FIL			

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	210 140
Operating temperature	Min Max	°C	-195 160
DRY			
Maximum sliding speed, U		m/s	0,13
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,05
Coefficient of friction, f			0,05 - 0,3*
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,15 - 0,4
Shaft surface hardness		НВ	> 350

<sup>\*</sup> Depending on operating conditions

# HPM Bearing Material



### FIBER REINFORCED COMPOSITE HYDRO BEARINGS

#### **CHARACTERISTICS**

- Designed for hydropower applications
- High load capacity
- Excellent shock and edge loading capacity
- Low-friction, superior wear rate and bearing life
- Excellent corrosion-resistance
- Dimensionally stable very low water absorption, low swelling
- Environmentally friendly



#### **AVAILABILITY**


#### Bearing forms available in standard dimensions:

- Plain cylindrical bushes

**Non-standard parts made-to-order:** Cylindrical bushes with non-standard dimensions, customized bearing designs

#### **APPLICATIONS**

**Industrial:** Servo-motor bearings, operating ring sliding segments, linkage bearings, wicket gate bearings, guide vane bearings, intake gate sliding segments, intake gate roller bearings, spillway gate bearings, trash rate bearings, fish screen bearings, trunnion bearings, blade bearings, injector bearings, deflector bearings, ball and butterfly trunnion bearings, etc.



OPERATING PERFORMANCE		
Dry	Very good	
Oil lubricated	Fair	
Grease lubricated	Poor	
Water lubricated	Very good	
Process fluid lubricated	Poor	


FOR SUPERIOR PEFORMANCE		
Oil lubricated	GAR-FIL / HPF	
Grease lubricated	DX / DX10	
Process fluid lubricated	GAR-FIL / HPF	

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	210 140
Operating temperature	Min Max	°C	-195 160
DRY			
Maximum sliding speed, U		m/s	0,13
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,23
Coefficient of friction, f			0,03 - 0,12*
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,2 - 0,8
Shaft surface hardness	Normal For longer service life	HB HB	> 180 > 480

<sup>\*</sup> Depending on operating conditions

## HPMB® Bearing Material





### HIGH PRECISION FIBER REINFORCED COMPOSITE BEARINGS

#### **CHARACTERISTICS**

- Machinable inner and outer diameters for superior application precision, circularity and cylindricity tolerances
- Pre-machined high precision HPMB bearings available for immediate installation
- High precision through easy single point machining of the bearing liner, on-site prior to installation
- Superior precision achieved with post-installation (inner diameter tolerance IT7 attainable) single point machining of the bearing liner
- High load capacity
- Excellent shock and edge loading capacity
- Low-friction with negligible stick-slip
- Low wear rate for extended bearing life


#### **AVAILABILITY**

**Bearing forms made-to-order:** Finished cylindrical bushings, pre-machined cylindrical bushings, flanged cylindrical bushings (subject to design review)

#### **APPLICATIONS**

**Industrial:** Railroad stabilization system, railroad brake linkages, injection molding machines – guide bushings, hydraulic cylinder pivots, water turbines – wicket gates, servomotors, links, water gates, valves

- Excellent corrosion-resistance
- Dimensionally stable very low water absorption, low swelling
- Environmentally friendly grease-free operation



OPERATING PERFORMANCE		
Dry	Very good	
Oil lubricated	Fair	
Grease lubricated	Not recommended	
Water lubricated	Very good	
Process fluid lubricated	To be tested by final user	

FOR SUPERIOR PEFORMANCE		
Oil lubricated	GAR-FIL / HPF	
Grease lubricated DX / DX10		
Process fluid GAR-FIL / lubricated HPF		

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	210 140
Operating temperature	Min Max	°C °C	-196 163
Coefficient of linear thermal	expansion	10 <sup>-6</sup> /K	12,6
DRY			
Maximum sliding speed, U		m/s	0,13
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,23
Coefficient of friction, f			0,03 - 0,12*
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,2 - 0,8
Shaft surface hardness	Normal For longer service life	HB HB	> 180 > 480

<sup>\*</sup> Depending on operating conditions

## HPF Bearing Material



### FIBER REINFORCED COMPOSITE BEARINGS WITH PTFE TAPE LINER

#### **CHARACTERISTICS**

- Proprietary filled PTFE tape machinable liner
- Designed for hydropower applications
- Machinable bearing surface
- High load capacity
- Excellent shock and edge loading capacity
- Low-friction, superior wear rate and bearing life
- Excellent corrosion-resistance
- Dimensionally stable very low water absorption, low swelling
- Environmentally friendly





#### **AVAILABILITY**


#### Bearing forms available in standard dimensions:

Plain cylindrical bushesSliding plates

**Non-standard parts made-to-order:** Cylindrical bushes with non-standard dimensions, customized bearing designs

#### **APPLICATIONS**

**Industrial:** Servo-motor bearings, operating ring sliding segments, linkage bearings, wicket gate bearings, guide vane bearings, intake gate sliding segments, intake gate roller bearings, spillway gate bearings, trash rate bearings, fish screen bearings, trunnion bearings, blade bearings, injector bearings, deflector bearings, ball and butterfly trunnion bearings, etc.



OPERATING PERFORMANCE	
Dry	Very good
Oil lubricated	Very good
Grease lubricated	Poor
Water lubricated	Very good
Process fluid lubricated	Good

FOR SUPERIOR PEFORM	ANCE
Grease lubricated	DX / DX10

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	140 140
Operating temperature	Min Max	°C	-195 140
DRY			
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,23
Coefficient of friction, f			0,02 - 0,1*
GREASE LUBRICATED			
Coefficient of friction, f			0,02 - 0,08*
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,2 - 0,8
Shaft surface hardness	Normal For longer service life	HB HB	> 180 > 480

<sup>\*</sup> Depending on operating conditions

### GGB-MEGALIFE® XT



### FIBER REINFORCED COMPOSITE PTFE THRUST WASHERS

#### **CHARACTERISTICS**

- Proprietary filled PTFE tape liner on both surfaces
- Excellent shock resistance
- High load capacity
- Excellent misalignment resistance
- Excellent contamination resistance
- Good surface speed capability
- Very good friction and wear properties
- Good chemical resistance



#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:

- Plain thrust washers

**Bearing forms made-to-order:** Thrust washers with non-standard dimensions

#### **APPLICATIONS**

**Industrial:** Pulley spacers, gear spacers, aerial lifts, fork lift masts, king pins, steering links, lift gates, cranes, backhoes, valve actuator linkages, etc.



OPERATING PERFORMANCE		
Dry	Very good	
Oil lubricated	Fair	
Grease lubricated	Poor	
Water lubricated	Very good	
Process fluid lubricated	Fair	

FOR SUPERIOR PEFORMANCE	
Oil lubricated	HPF
Grease lubricated	DX
Process fluid lubricated	HPF

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm <sup>2</sup> N/mm <sup>2</sup>	140 140
Operating temperature	Min Max	°C	-195 175
DRY			
Maximum sliding speed, U		m/s	0,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,23
Coefficient of friction, f			0,02 - 0,12*
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,4
Shaft surface hardness	Normal	НВ	> 200

<sup>\*</sup> Depending on operating conditions

# Multifil Bearing Material



### PROPRIETARY FILLED PTFE SLIDING BEARING TAPE

#### **CHARACTERISTICS**

- Superior sliding bearing material which can be easily bonded to any clean, rigid substrate
- Reduces vibration



#### **AVAILABILITY**

Bearing forms available in standard dimensions:

- Bearing tape

Tape with 0,015" to 0,125" (0,38 to 3,2 mm) thickness and 12" (305 mm) width or 24" (610 mm) width

#### **APPLICATIONS**

Industrial: Machine tool ways, gibs and other sliding applications



OPERATING PERFORMANCE	
Dry	Very good
Oil lubricated	Very good
Grease lubricated	Very good
Water lubricated	Good
Process fluid lubricated	Good

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	70 35
Operating temperature	Min Max	°C °C	-200 280
DRY			
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	0,32
Coefficient of friction, f			0,07
GREASE / OIL LUBRICATED			
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,25
Coefficient of friction, f			0,05
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,2 - 0,4
Shaft surface hardness		НВ	> 200

# SBC with GAR-MAX® Bearing Material



#### AVAILABILITY

**Bearing forms made-to-order:** GGB SBC with GAR-MAX® sealed assemblies with or without steel outer shell, customized bearing designs


#### **APPLICATIONS**

**Industrial:** Steering linkages, hydraulic cylinder pivots, king pin bearings, boom lifts, scissor lifts, cranes, hoists, lift gates, backhoes, trenchers, skid steer loaders, front end loaders, etc.

### SEALED FIBER REINFORCED COMPOSITE BEARINGS

#### **CHARACTERISTICS**

- Self-lubricating bearings
- High static load capacity
- Excellent resistance to shock loading and misalignment
- Very good friction and wear properties
- Good chemical resistance
- Sealed to exclude contaminates to offer extended service life
- Environmentally friendly and eliminates need for automated grease system and grease



OPERATING PERFORMANCE	
Dry	Very good
Oil lubricated	Fair
Grease lubricated	Fair
Water lubricated	Fair
Process fluid lubricated	Fair

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	210 140
Operating temperature	Min Max	°C °C	93 104
DRY			
Maximum sliding speed, U		m/s	0,13
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,05
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,15 - 0,4
Shaft surface hardness	Normal For longer service life	HB HB	> 350 > 480

# SBC with HSG Bearing Material



### SEALED FIBER REINFORCED COMPOSITE BEARINGS

#### **CHARACTERISTICS**

- Self-lubricating bearings
- High static load capacity
- Excellent resistance to shock loading and misalignment
- Very good friction and wear properties
- Good chemical resistance
- Sealed to exclude contaminates to offer extended service life
- Environmentally friendly and eliminates need for automated grease system and grease




#### **AVAILABILITY**

**Bearing forms made-to-order:** GGB SBC with HSG sealed assemblies with or without steel outer shell, customized bearing designs

#### **APPLICATIONS**

**Industrial:** Steering linkages, hydraulic cylinder pivots, king pin bearings, boom lifts, scissor lifts, cranes, hoists, lift gates,backhoes, trenchers, skid steer loaders, front end loaders, etc.



OPERATING PERFORMANCE	
Dry	Very good
Oil lubricated	Fair
Grease lubricated	Fair
Water lubricated	Fair
Process fluid lubricated	Fair

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	415 140
Operating temperature	Min Max	°C	93 104
DRY			
Maximum sliding speed, U		m/s	0,13
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,05
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,15 - 0,4
Shaft surface hardness	Normal For longer service life	HB HB	> 350 > 480

# GGB-CSM® Bearing Material



### THICK WALLED MONOMENTAL BEARINGS

#### **CHARACTERISTICS**

- Self-lubricating metal bearings produced by metallurgic powder
- Maintenance-free bearings with homogeneously distributed solid lubricant (graphite, MoS<sub>2</sub>) in the metallic matrix
- High load capacity and temperature ranges up to 600°C possible depending on the alloy
- Corrosion-resistant alloys are available
- Lead-free alloys are available







#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes, flanged bushes, thrust washers, sliding plates, half-bearings, axial and radial segment rings, self-aligning spherical bearings, special shapes, customized bearing designs

#### **APPLICATIONS**

Industrial: General mechanical engineering, applications with elevated temperatures and corrosion risk, exhaust or smoke flaps, valves, turbines, iron foundry, steel and aluminum industry, furnaces, blower, steel works and civil engineering, turbines (water, steam and gas), pumps and compressors, sewage purification plants, thermal treatment furnaces, hot rolling mills, food and beverage industry, packaging equipment, agriculture and construction machines, handling equipment, tire molds, etc.

#### **MICROSECTION**



OPERATING PERFORMANCE			
Dry	Good		
Oil lubricated	Good		
Grease lubricated	Good		
Water lubricated	Depending on alloy		
Process fluid lubricated	Depending on fluid or alloy		

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	100 - 260 55 - 130
Operating temperature	Min Max	°C	-200 600
Coefficient of linear thermal expansion		10 <sup>-6</sup> /K	13 - 18
DRY			
Maximum sliding speed, U		m/s	0,2 - 0,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	0,8 - 1,5
Coefficient of friction, f			0,11 - 0,5
WATER LUBRICATED			
Coefficient of friction, f			0,08 - 0,18
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,2 - 0,8
Shaft surface hardness		HB HRC	> 180 > 45

Bearing properties and recommendations dapending on GGB-CSM material grade

# GGB-CBM® Bearing Material



### THIN WALLED BIMETAL BEARINGS MADE BY METALLURGIC POWDER

#### **CHARACTERISTICS**

- Self-lubricating and maintenance-free with homogeneously distributed solid lubricant (graphite) in the sliding layer
- High load capacity and suited to temperatures from -150°C up to 280°C
- Different metallic backings are available: stainless steel, carbon steel or bronze
- Lead-free alloys are available







#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes, flanged bushes, thrust washers, axial washers, sliding plates, half shells, axial and radial segment rings, spherical bushings, customized bearing designs

#### **APPLICATIONS**

**Industrial:** General mechanical engineering, applications at high loads, iron foundry, steel and aluminum industry, furnaces, blower, steel works, food and beverage industry, packaging equipment, agriculture and construction machines, handling equipment, tire molds, etc.

#### **MICROSECTION**



OPERATING PERFORMANCE		
Dry	Good	
Oil lubricated	Good	
Grease lubricated	Good	
Water lubricated	Good	
Process fluid lubricated	Depending on fluid	

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	260 - 280 80 - 150
Operating temperature	Min Max	°C °C	-150 280
Coefficient of linear thermal expansion		10 <sup>-6</sup> /K	12 - 16
DRY			
Maximum sliding speed, U		m/s	0,3 - 0,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	0,5 - 1,0
Coefficient of friction, f			0,10 - 0,2
WATER LUBRICATED			
Coefficient of friction, f			0,10 - 0,15
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,2 - 0,8
Shaft surface hardness		НВ	> 180 - > 250

Bearing properties and recommendations dapending on GGB-CBM material grade

# GGB-BP25 Bearing Material



### METAFRAM OIL IMPREGNATED SINTERED BRONZE BEARINGS

#### **CHARACTERISTICS**

- Similar to SINT A 50, impregnation group 1
- Maintenance-free bearing for general engineering applications
- Optimum performance under relatively light loads and high speeds
- Produced by powder metallurgy process and therefore suitable for complex shapes





#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:


Plain cylindrical bushes
 Plain flanged bushes

**Non-standard parts made-to-order:** Cylindrical bushes and flanged bushes with non-standard dimensions, spherical bearings, tubes and rod blanks, customized bearing designs

#### **APPLICATIONS**

Industrial: FHP motor bearings, domestic appliances and hand tools

#### **MICROSECTION**



BP25 with composition
Sn 8 - 10,5 %
Other < 2 %
Cu Rest
Impregnation group 1
(up to 80°C)

OPERATING PERFORMANCE			
Dry	Good (PTFE / MoS <sub>2</sub> )		
Oil lubricated	Good		
Grease lubricate	ed Fair		
Water lubricated	Not recommended		
Process fluid lubricated	Not recommended		
lubricated			

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	20 10
Operating temperature	Min Max	°C	-180 / 0* 90 / 300*
Minimum density		g/cm³	6,2
Minimum apparent porosity		%	23
OIL IMPREGNATED			
Maximum sliding speed, U		m/s	0,1 - 6,0*
Maximum pU factor		N/mm <sup>2</sup> x m/s	0,1 - 1,8*
Coefficient of friction, f			0,05 - 0,25*
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,3 - ≤ 0,6*
Shaft surface hardness		НВ	> 240 - > 355*

# GGB-FP20 Bearing Material



### METAFRAM OIL IMPREGNATED SINTERED IRON BEARINGS

#### **CHARACTERISTICS**

- Similar to SINT A 50, impregnation group 1
- Maintenance-free bearing for general engineering applications
- Optimum performance under relatively light loads and high speeds
- Produced by powder metallurgy process and therefore suitable for complex shapes




#### **AVAILABILITY**

**Non-standard parts made-to-order:** plain cylindrical bushes, plain flanged bushes, non standard parts

#### **APPLICATIONS**

Industrial: FHP motor bearings, domestic appliances and hand tools

#### **MICROSECTION**



Cu 1 - 4 %
C < 0,25 %
Other < 2%
Rest Fe
Impregnation
group 1
(up to 80°C)

OPERATING PERFORMANCE			
<b>Dry</b> G	Good (PTFE / MoS <sub>2</sub> )		
Oil lubricated	Good (Oil impregnated)		
Grease lubricated	Not recommended		
Water lubricated	Not recommended		
Process fluid lubricated	Not recommended		

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	45 8,0 - 22,5
Operating temperature	Min Max	°C	-180 / -5* 90 / 300*
Minimum density		g/cm³	5,6
Minimum apparent porosity		%	20
OIL IMPREGNATED			
Maximum sliding speed, U		m/s	0,1 - 4,0*
Maximum pU factor		N/mm <sup>2</sup> x m/s	0,1 - 1,8*
Coefficient of friction, f			0,05 - 0,25*
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,2 - ≤ 0,3*
Shaft surface hardness		НВ	> 240 - > 355*

# GGB-S016 Bearing Material



### METAFRAM OIL IMPREGNATED SINTERED IRON BEARINGS

#### **CHARACTERISTICS**

- Maintenance-free bearing for general engineering applications
- Superior performance compared to GGB-FP20 under high loads and low speeds
- Produced by powder metallurgy process and therefore suitable for complex shapes



#### **AVAILABILITY**

Blanks are made-to-order

#### **APPLICATIONS**

**Industrial:** FHP motor bearings, domestic appliances and hand tools, heavy duty applications: construction equipment, railway equipment, military equipment

#### **MICROSECTION**



Cu 20 % C 0,3 - 0,6 % Other < 2% Rest Fe

OPERATING PERFORMANCE		
Dry	Not applicable	
Oil lubricated	Good (Oil impregnated)	
Grease lubricated	Not recommended	
Water lubricated	Not recommended	
Process fluid lubricated	Not recommended	

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	120 60
Operating temperature	Min Max	°C	0 105
Minimum density		g/cm <sup>3</sup>	6
Minimum apparent porosity		%	16
OIL IMPREGNATED			
Maximum sliding speed, U		m/s	0,3
Maximum pU factor		N/mm <sup>2</sup> x m/s	0,9
Coefficient of friction, f			0,05 - 0,15*
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,2*
Shaft surface hardness		НВ	> 355

# GGB-SHB® Bearing Material



### CASE HARDENED STEEL BEARINGS

#### **CHARACTERISTICS**

- For lubricated applications
- With plain or grooved sliding layer
- Suitable for grease lubrication
- Low rotation speed with high specific pressure







#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:

- Plain cylindrical bushes

**Non-standard parts made-to-order:** bearings with various lubrication grooves, non-standard parts

#### **APPLICATIONS**

**Industrial:** Earth moving machinery, excavators and loaders, farming machinery, power harrows, ploughs and harvesters, grabs, buckets and grippers, hydraulic cylinders for the protection against wear of bottoms and eyelets, industrial washing machines, sliding guides for industrial presses, suction pumps, sliding seats, machine tools

#### **MICROSECTION**



Steel E410, E470 (20MnV6, AISI A381) acc. to EN 10305

OPERATING PERFORMANCE		
Dry	Poor	
Oil lubricated	Good	
Grease lubricated	Very good	
Water lubricated	Not recommended	
Process fluid lubricated	Depending on fluid	

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	300 150
Tensile strength		N/mm²	550
Operating temperature	Min	°C	150
Density			7,8
Coefficient of linear thermal expansion		%	12
GREASE LUBRICATED			
Maximum sliding speed, U		m/s	0,1
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,5
Coefficient of friction, f			0,2
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,8
Shaft surface hardness		HRC	58 - 62

# AuGlide Bearing Material



### BIMETAL LEAD-FREE PLAIN BEARINGS

#### **CHARACTERISTICS**

- Lead-free
- Machinable
- Design freedom customizable to meet specific indentation and shape needs
- Capable of supporting high specific loads and high temperatures
- Excellent fatigue strength under dynamic and shock load conditions
- Excellent wear resistance
- Suitable for hydrodynamic operation
- Suitable for oil and grease lubrication









#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes and sliding plates with non-standard dimensions, RoHS customized bearing designs

#### **APPLICATIONS**

**Automotive:** Transmissions, king pin, truck brake caliper **Industrial:** Agricultural machinery, earth-movers, textile machinery, pneumatic equipment, mechanical handling and lifting equipment, hydraulic cylinders, offhighway equipment, and many more.

- Superior performance under oscillating movement
- Thin-wall construction permits compact bearing assembly
- Indents in the bearing surface provide a reservoir for grease and thus allow extended re-greasing



OPERATING PERFORMANCE		
Dry	Poor	
Oil lubricated	Good	
Grease lubricated	Very good	
Water lubricated	Poor	
Process fluid lubricated	Poor	

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	300 140
Operating temperature	Min Max greased Max oil lubricated	°C °C	- 40 150 250
OIL LUBRICATED			
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	2,8
Coefficient of friction, f	Greased Oil		0,05 - 0,12 0,04 - 0,12
RECOMMENDATIONS			
Shaft surface roughness, Ra	Normal	μm	≤ 0,8
Shaft surface hardness	Normal For longer service life		> 200 HB > 350 HB

# SY Bearing Material



#### BIMETAL PLAIN BEARINGS TO STANDARD SAE 792

#### **CHARACTERISTICS**

- Bimetal bearing with steel backing and bronze overlay
- Particularly suitable for high specific loads with oscillating motion and low frequency
- Applicable in rough operation conditions
- High load capacity, very good resistance to fatigue strength at higher temperatures

#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:


- Cylindrical bushes - Thrust washers

**Bearing forms made-to-order:** Cylindrical bushes and thrust washers with non-standard dimensions, sliding plates, customized bearing designs

#### **APPLICATIONS**

**Industrial:** Mechanical handling and lifting equipment, hydraulic cylinders, agricultural equipment, off highway equipment etc.

#### **MICROSECTION**



OPERATING PERFORMANCE	
Dry	Poor
Oil lubricated	Good
Grease lubricated	Very good
Water lubricated	Poor
Process fluid lubricated	Poor

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	300 140
Operating temperature	Min Max greased Max oil lubricated	°C °C	-40 150 250
OIL IMPREGNATED			
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	2,8
Coefficient of friction, f	Greased Oil lubricated		0,05 - 0,12 0,04 - 0,12
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,8
Shaft surface hardness	Normal For longer service life	HB HB	> 200 > 350

# SP Bearing Material



#### **BIMETAL PLAIN BEARINGS TO STANDARD SAE 794**

#### **CHARACTERISTICS**

- Bimetal bearing with steel backing and leaded bronze overlay
- For lubricated applications with plain sliding layer
- Suitable for oil and grease lubrication


#### **AVAILABILITY**

Bearing forms made-to-order: Cylindrical bushes, thrust washers, sliding plates, customized bearing designs

#### **APPLICATIONS**

Industrial: Mechanical handling and lifting equipment, machine slides, hydraulic cylinders, hydraulic motors, pneumatic equipment, medical equipment, textile machinery, agricultural equipment, etc.

#### **MICROSECTION**



Sliding Layer CuPb26Sn2 consists of Approx. Cu 72 % Pb 26 %

OPERATING PERFORMANCE	
Dry	Poor
Oil lubricated	Good
Grease lubricated	Good
Water lubricated	Poor
Process fluid lubricated	Poor

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	250 120
Operating temperature	Min Max greased Max oil lubricated	°C °C °C	-40 150 250
GREASED / OIL LUBRICATED	)		
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	2,8
Coefficient of friction, f	Greased Oil lubricated		0,05 - 0,12 0,04 - 0,12
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,4
Shaft surface hardness	Normal For longer service life	HB HB	> 200 > 350

# MBZ-B09 Bearing Material



### BRONZE BEARINGS MADE OF CuSn8 WITH LUBRICATION INDENTS

#### **CHARACTERISTICS**

- Bearing material made of solid bronze strip with indents for lubrication
- Good wear resistance, suitable for rough conditions
- Optimum performance under relatively high loads and low speeds





#### **AVAILABILITY**

#### Bearing forms available in standard dimensions:

- Cylindrical bushes

**Bearing forms made-to-order:** Cylindrical bushes with non-standard dimensions, flanged dimensions, flanged bushes, sliding plates, customized bearing designs

#### **APPLICATIONS**

**Industrial:** Mechanical handling and lifting equipment, hydraulic cylinders, pneumatic equipment, medical equipment, textile machinery, agricultural equipment, etc.

#### **MICROSECTION**



CuSn8 with Composition Sn 8 % P < 0,05 % Cu Rest

OPERATING PERFORMANCE	
Dry	Poor
Oil lubricated	Good
Grease lubricated	Good
Water lubricated	Poor
Process fluid lubricated	Poor

BEARING PROPERTIES	,	UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	120 40
Operating temperature	Min Max greased Max oil lubricated	°C °C	-40 150 250
GREASED / OIL LUBRICATED	)		
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	2,8
Coefficient of friction, f			0,06 - 0,15
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,8
Shaft surface hardness	Normal For longer service life	HB HB	> 200 > 350

# LD® Bearing Material



#### **BRONZE BEARINGS MADE OF CuSn8** WITH GREASE RESERVOIRS

#### **CHARACTERISTICS**

- Wear resistant bearing made of solid bronze strip with perforation for lubricated applications
- Improved performance compared with MBZ-B09: larger grease reservoirs increase maintenance intervals, dirt and debris swept into perforations, thereby reducing wear
- Optimum performance under relatively high loads and low speeds




#### **AVAILABILITY**

Bearing forms made-to-order: Cylindrical bushes with nonstandard dimensions, customized bearing designs

#### **APPLICATIONS**

**Industrial:** Mechanical handling and lifting equipment, hydraulic cylinders, pneumatic equipment, medical equipment, textile machinery, agricultural equipment, etc.

#### **MICROSECTION**



CuSn8 with Composition Sn 8 % P < 0,05 %

OPERATING PERFORMANCE	
Dry	Poor
Oil lubricated	Fair
Grease lubricated	Good
Water lubricated	Poor
Process fluid lubricated	Poor

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	120 40
Operating temperature	Min Max greased	°C	-40 150
GREASED / OIL LUBRICATED	)		
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		$N/mm^2 x m/s$	2,8
Coefficient of friction, f			0,06 - 0,15
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,8
Shaft surface hardness	Normal For longer service life	HB HB	> 200 > 350

# LDD® Bearing Material



### BRONZE BEARINGS MADE OF CuSn8 WITH GREASE RESERVOIRS

#### **CHARACTERISTICS**

- Wear resistant, perforated bronze bearing material with integrated seals for lubricated applications
- Integrated lip seals reduce installation space, protect the bearing from contamination and prolong service life after greasing
- Suitable for use with all standard greases
- Optimum performance under relatively high loads and low speeds



#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes with non-standard dimensions, customized bearing designs

#### **APPLICATIONS**

**Industrial:** Mechanical handling and lifting equipment, hydraulic cylinders, pneumatic equipment, medical equipment, textile machinery, agricultural equipment, etc.

#### **MICROSECTION**



CuSn8 with Composition Sn 8 % P < 0,05 % Cu Rest

OPERATING PERFORMANCE		
Dry	Not recommended	
Oil lubricated	Fair	
Grease lubricated	l Good	
Water lubricated	Poor	
Process fluid lub	ricated Poor	

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	120 40
Operating temperature	Min Max greased	°C	-40 150
GREASED / OIL LUBRICATE	D		
Maximum sliding speed, U		m/s	2,5
Maximum pU factor		$N/mm^2 x m/s$	2,8
Coefficient of friction, f			0,06 - 0,15
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	≤ 0,8
Shaft surface hardness	Normal For longer service life	HB HB	> 200 > 350

# GGB-DB® Bearing Material



### CAST BRONZE BEARINGS WITH SOLID LUBRICANT INSERTS

#### **CHARACTERISTICS**

- Maintenance-free bearing material for heavy duty applications
- Excellent performance under high loads and intermittent operation
- Also available with graphite inserts for temperatures above 250°C




#### **AVAILABILITY**

**Bearing forms made-to-order:** Cylindrical bushes, flanged bushes, thrust washers, sliding plates, pintle bearings, half-bearings, axial and radial segment rings, self-aligning spherical bearings, customized bearing designs

#### **APPLICATIONS**

**Industrial:** Offshore industry, underwater equipment, bridges and civil engineering, iron and steel industry equipment, cranes and conveyors, deep and open cast mining equipment, construction and earthmoving equipment, etc.



OPERATING PERFORMANCE	
Dry	Good
Oil lubricated	Good
Grease lubricated	Good
Water lubricated	Good
Process fluid lubricated	Fair

BEARING PROPERTIES		UNITS	VALUE
GENERAL			
Maximum load, p	Static Dynamic	N/mm² N/mm²	200 100
Operating temperature	Min Max greased	°C °C	-50 350
DRY			
Maximum sliding speed, U		m/s	0,5
Maximum pU factor		N/mm <sup>2</sup> x m/s	1,5
Coefficient of friction, f			0,05 - 0,18
RECOMMENDATIONS			
Shaft surface roughness, Ra		μm	0,2 - 0,8
Shaft surface hardness	Normal	НВ	> 200

# UNI Self-Aligning Bearing Housing



### SELF-ALIGNING PILLOW BLOCK BEARING HOUSING

#### **CHARACTERISTICS**

- Adjusting bearing for misalignment equalisation
- All-purpose as flange or pedestal bearing, suitable for high loads
- Self-aligning spheric avoids edge load to the bearing
- Adjustable up to ± 5°
- Spheric is secured against distortion
- Depending on choice of housing, spherics and bearings, simple to most demanding bearing solutions are possible
- For optimum design solutions, various bearings from the GGB product program are applicable



Housing Material: **GGG40** Spherical Material: **16MnCr5** 

Corrosion-resistant material possible

#### **AVAILABILITY**

Made-to-order

#### **APPLICATIONS**

**Industrial:** Wind energy plants, car washes, cleaning machines, drum systems, bevelling equipment, handling systems, conveyor belts (pulleys), printing machines, heating and ventilation equipment, hoists, cranes, textile machinery, special machine engineering, bakery equipment, marine equipment

LOAD LIMIT VALUES	FOR RADIAL FORCES			
SIZE	BUSH ID	MAX RADIAL LOAD [N] (HOUSING)	MAX RADIAL LOAD [N] (BOLT)	MAX SHEAR OFF LOAD [N] (BOLT)
1	10 - 25	20 000	10 000	1 000
2	28 - 40	30 000	15 000	1 500
3	45 - 60	50 000	25 000	2 500
4	65 - 80	90 000	45 000	4 500
5	85 - 100	125 000	62 500	6 000

The given data for UNI bearing housings are valid for 12.9 screws (DIN EN 20898, part 1), since the housing stability exceeds the permissible load of the fixing screws.

# MINI Self-Aligning Bearing Housing



Housing Material: **AIMgSi12** Spherical Material: **9SMn28K** 

Stainless steel and other materials available

#### **AVAILABILITY**

Made-to-order

#### **APPLICATIONS**

Industrial: Wind energy plants, car washes, cleaning machines, drum systems, bevelling equipment, handling systems, conveyor belts (pulleys), printing machines, heating and ventilation equipment, hoists, cranes, textile machinery, special machine engineering, bakery equipment, marine equipment

### SELF-ALIGNING PILLOW BLOCK BEARING HOUSING

#### **CHARACTERISTICS**

- Adjusting bearing for misalignment equalisation
- All-purpose as flange or pedestal bearing, suitable for high loads
- Self-aligning spheric avoids edge load to the bearing
- Adjustable up to ± 5°
- Spheric is secured against distortion
- Depending on choice of housing, spherics and bearings, simple to most demanding bearing solutions are possible
- For optimum design solutions, various bearings from the GGB product program are applicable

LOAD LIMIT VALUES	FOR RADIAL FORCES			
SIZE	BUSH ID	MAX RADIAL LOAD [N] (HOUSING)	MAX RADIAL LOAD [N] (BOLT)	MAX SHEAR OFF LOAD [N] (BOLT)
0	8 - 15	10 000	5 000	500

The permissible loads for MINI bearings housings are defined by the housing stability or the strength of the fixing screws (6mm diameter), depending on the load direction.

# EXALIGN® Self-Aligning Bearing Housing





Housing Material: **Cast Iron** Spherical Material: **Cast Iron** 

Corrosion-free and corrosion-resistant models possible

#### **AVAILABILITY**

Made-to-order

#### **APPLICATIONS**

Industrial: Wind energy plants, car washes, cleaning machines, drum systems, bevelling equipment, handling systems, conveyor belts (pulleys), printing machines, heating and ventilation equipment, hoists, cranes, textile machinery, special machine engineering, bakery equipment, marine equipment

### SELF-ALIGNING PEDESTAL AND FLANGE BEARING HOUSING

#### **CHARACTERISTICS**

- Adjusting bearing for misalignment equalisation
- All-purpose as flange (EXALIGN® DF and FL) or pedestal bearing (EXALIGN® PB), suitable for high loads
- Self-aligning spheric avoids edge load to the bearing
- Adjustable up to ± 5°
- Spheric is secured against distortion
- Depending on choice of housing, spherics and bearings, simple to most demanding bearing solutions are possible
- For optimum design solutions, various bearings from the GGB product program are applicable

LOAD LIMIT VALUES FOR RADIAL FORCES		TYPE PB 2-HOLE PEDESTAL BEARING	TYPE FL/DF 4-HOLE / 2-HOLE FLANGE BEARING	
SIZE	BUSH ID	MAX RADIAL LOAD [N]	MAX RADIAL LOAD [N]	
1	10 - 15	4 250	3 750	
2	20 - 25	7 700	5 900	
3	30	9 500	8 000	
4	35 - 40	17 000	11 000	
5	45	23 000	12 000	
6	50	25 000	14 500	
7	55 - 60	30 000	16 000	
8	70 - 75	38 000	17 000	
9	80 - 85	45 500	27 000	
10	90 - 100	74 500	30 500	

# Bearing Application Data Sheet



Please complete the form below and share it with your GGB sales engineer or send it to: <a href="mailto:india@ggbearings.com">india@ggbearings.com</a>

DATA FOR BEARING DESIGN CALCU Application:	LATION							
Project/No.:	Quantity:		New Des	sign	Exis	ting Design		
Steady load Rotating load	Rotational move	ment	Oscillatir	ng movement	Line	ar movement		
BEARING TYPE	DIMENSIONS [MM]			FITS & TOLERANO	CES			
	Inside diameter	Di		Shaft	D <sub>J</sub>			
Ush B	Outside diameter	Do		Bearing housing	D <sub>H</sub>			
Dusii	Length	В	_					
	Flange Diameter	D <sub>fl</sub>		OPERATING ENVIR		Т		
##100	Flange thickness	B <sub>fl</sub>		Ambient temperature	· T <sub>amb</sub> [°]			
	Wall thickness	S <sub>T</sub>	_	Bearing housing mat	erial			
<u> </u>	Length of slideplate	L		Housing with good h	neating tran	sfer properties		
	Width of slideplate	W		Light pressing or ins	sulated hou	sing with poor		
Flanged bush B	Thickness of slideplate	Ss		heat transfer proper	ties			
Bfl	LOAD	LOAD			Non metal housing with poor heat transfer properties			
	Static load			Alternate operation	in water an	d dry		
°       -   -   -   -   -   -   -	Dynamic load			LUBRICATION				
م الماسية الما	Axial load F	[N]						
	Radial load F	[N]		Dry				
<u> </u>	NAOVENAENT			Continuous lubricat				
	MOVEMENT	1 /:-1		Process fluid lubric	ation			
Thrust washer		1/min]		Initial lubrication on	ly			
	·	[m/s]		Hydrodynamic cond	litions			
<b>A</b>		[mm]		Process fluid				
	·	1/min]		Lubricant				
	Oscillating $\phi$ $\phi$ [°] cycle		_	Dynamic viscosity η[mPas]				
<u>*  </u>	-()-			SERVICE HOURS	PER DAY			
<u> </u>				Continuous operation	ı			
Slideplate	Osc. frequence N <sub>osz</sub> [1	1/min]		Intermittent operation	n			
				Operating time				
S	MATING SURFACE			Days per year				
<u> </u>	Material			050//051155				
'   <del>&lt;                                   </del>		B/HRC		SERVICE LIFE	r [1.1			
>	Surface finish Ra	a [µm]		Required service life	L <sub>H</sub> [h]			
<u> </u>	CUSTOMER INFORMAT	ION						
	Company							
Special parts (sketch)	Street							
	City / State / Province / F							
	Telephone							
	Name							

### Product Information

GGB gives an assurance that the products described in this document have no manufacturing errors or material deficiencies.

The details set out in this document are registered to assist in assessing the material's suitability for the intended use. They have been developed from our own investigations as well as from generally accessible publications. They do not represent any assurance for the properties themselves.

Unless expressly declared in writing, GGB gives no warranty that the products described are suited to any particular purpose or specific operating circumstances. GGB accepts no liability for any losses, damages or costs however they may arise through direct or indirect use of these products.

GGB's sales and delivery terms and conditions, included as an integral part of quotations, stock and price lists, apply absolutely to all business conducted by GGB. Copies can be made available on request.

Products are subject to continual development. GGB retains the right to make specification amendments or improvements to the technical data without prior announcement.

Edition 2023 (This edition replaces earlier editions which hereby lose their validity).

#### STATEMENT REGARDING LEAD CONTENT IN GGB PRODUCTS & EU DIRECTIVE COMPLIANCE

GGB is committed to adhering to all U.S., European and international standards and regulations with regard to lead content. We have established internal processes that monitor any changes to existing standards and regulations, and we work collaboratively with customers and distributors to ensure that all requirements are strictly followed. This includes RoHS and REACH guidelines.

GGB makes it a top priority to operate in an environmentally conscious and safe manner. We follow numerous industry best practices, and are committed to meeting or exceeding a variety of internationally recognized standards for emissions control and workplace safety.

Each of our global locations has management systems in place that adhere to IATF 16949, ISO 9001, ISO 14001 and ISO 45001 quality regulations.

All of our certificates can be found here: <a href="https://www.ggbearings.com/en/company/certificates">https://www.ggbearings.com/en/company/certificates</a>. A detailed explanation of our commitment to REACH and RoHS directives can be found at <a href="https://www.ggbearings.com/en/company/quality-and-environment">https://www.ggbearings.com/en/company/quality-and-environment</a>.

#### **FABRICATION**

At temperatures up to 250°C the polytetrafluroethylene (PTFE) present in the lining material is completely inert so that even on the rare occasions in which DP4, DP4-B, DP10 or DP11 bushes are drilled or sized after assembly there is no danger in boring or burnishing.

At higher temperatures however, small quantities of toxic fumes can be produced and the direct inhalation of these can cause an influenza type of illness which may not appear for some hours but which subsides without after-effects in 24-48 hours.

Such fumes can arise from PTFE particles picked up on the end of a cigarette. Therefore smoking should be prohibited where DP4, DP4-B, DP10 or DP11 are being machined.

GGB®, DP4®, DP4-B, DU®, DU-B, DP10, DP11, DP31, DX®, DX®10, HI-EX®, DTS10®, DS, EP®, EP®12, EP®15, EP®22, EP®30, EP®43, EP®44, EP®63, EP®64, EP®73, EP®79, FLASH-CLICK, KA Glacetal, Multilube, GAR-MAX®, GAR-FIL, HSG, MLG, HPM, HPMB®, HPF, GGB-MEGALIFE® XT, Multifil, SBC with GAR-MAX®, SBC with HSG, GGB-CSM®, GGB-CBM®, GGB-BP25, GGB-FP20, GGB-SHB®, GGB-SO16, AuGlide, SY, SP, GGB-DB®, UNI, MINI and EXALIGN® are registered trademarks or trademarks, as the case may be, of GGB and its affiliates.

Any use of GGB's trademarks without GGB's prior written permission is strictly prohibited.

MBZ-B09, LD® and LDD® are the names of products of Wieland-Werke AG, Germany.

©2023 GGB. All rights reserved.

# PUSHING BOUNDARIES TO CO-CREATE A HIGHER QUALITY OF LIFE









#### **GGB INDIA**

Timken GGB Technology Private Limited A-88/89, 'H' Block, MIDC IND-Pimpri Pune - 411018, Maharashtra Tel. +91 20 6712 6652 www.ggbearings.com



PP100ENG04-23IND